

D. Dupont, D. Depuydt, K. Binnemans

*Journal of Physical Chemistry B* **119**, 6747–6757 (2015).

# Overview of the Effect of Salts on Biphasic Ionic Liquid/Water Solvent Extraction Systems: Anion Exchange, Mutual Solubility and Thermomorphic Properties

*David Dupont<sup>a</sup>, Daphne Depuydt<sup>a</sup>, Koen Binnemans<sup>a\*</sup>*

<sup>a</sup>KU Leuven, Department of Chemistry, Molecular Design and Synthesis, Celestijnenlaan 200F,  
P.O. Box 2404, B-3001 Heverlee, Belgium.


## Abstract

Hydrophobic (water-immiscible) ionic liquids (ILs) are frequently used as organic phase in solvent extraction studies. These biphasic IL/water extraction systems often also contain metal salts or mineral acids, which can significantly affect the IL through (un)wanted anion exchange and changes in the solubility of IL in the aqueous phase. In the case of thermomorphic systems, variations in the cloud point temperature are also observed. All these effects have important repercussions on the choice of IL, suitable for a certain extraction system. In this paper, a complete overview of the implications of metal salts on biphasic IL/water systems is given. Using the Hofmeister series as a starting point, a range of intuitive prediction models are introduced, supported by experimental evidence for several hydrophobic ILs, relevant to solvent extraction. Particular emphasis is placed on the IL betainium bis(trifluoromethylsulfonyl)imide [Hbet][Tf<sub>2</sub>N]. The aim of this work is to provide a comprehensive interpretation of the observed effects of metal salts, so that it can be used to predict the effect on any given biphasic IL/water system instead of relying on case-by-case reports. These prediction tools for the impact of metal salts can be useful to optimize IL synthesis procedures, extraction systems and thermomorphic properties. Some new insights are also provided for the rational design of ILs with UCST or LCST behavior based on the choice of IL anion.

## Introduction

The study of the effect of metal salts on the behavior of compounds in solution starts with Franz Hofmeister in 1888. He described the effect of salt cations and anions on the stability and solubility of the protein ovalbumin in aqueous solutions, and ranked the ions in the so-called *Hofmeister series*.<sup>1</sup> His observations were later transposed to explain the effect of metal salts and organic salts on the behavior of other proteins, colloids, and polymers in solution.<sup>2-22</sup> Ions that promote the dissolution of a compound in solution are called *salting-in ions*, while ions that exclude a solute from solution are called *salting-out ions*.<sup>2-22</sup> Despite the apparent simplicity of this theory, it still continues to puzzle scientists to this day.<sup>23-24</sup> The importance of this complicated solvation science is becoming ever more apparent as the study of interfacial phenomena and solvent structure on a molecular level is the key to understanding many areas of chemistry.<sup>22-33</sup> Due to their strongly ionic character, ILs have received particular attention lately in this area of solvation science.<sup>34</sup> Under the influence of salts, some *water-miscible* ILs can form IL-based aqueous biphasic systems (ABS).<sup>34-49</sup> More importantly, the properties of biphasic IL/water systems formed by *water-immiscible* ILs are also greatly affected by the addition of metals and mineral acids.<sup>50-56</sup> These water-immiscible ionic liquids (ILs) have shown great promise as organic phase in solvent extraction studies. The ILs can be used as diluents for extractants or task-specific ILs can be prepared in which a functional (extracting) group is incorporated in the structure of the IL.<sup>57</sup> Due to the infinite number of possible anion and cation combinations, ILs are often considered designer or task-specific solvents.<sup>58</sup> A well-known example is the carboxyl-functionalized IL betainium bis(trifluorosulfonyl)imide [Hbet][Tf<sub>2</sub>N] which can be used for the extraction of a range of metal ions.<sup>59-64</sup> In traditional solvent extraction, which uses apolar solvents such as toluene or kerosene as organic phase, the effect of metal salts is mostly visible in the mutual solubility of the organic

phase and aqueous phase.<sup>65</sup> The solubility of uncharged hydrophobic molecules such as benzene or toluene in the aqueous phase can be increased by the adsorption of ions which counters the van der Waals attraction between the hydrophobic solutes.<sup>10,66</sup> Both anions and cations are effective at increasing the surface charge and improving their solubility by countering the van der Waals attraction. The effect of ions is therefore only related to their hydrophobicity since this will determine if they can adsorb on the hydrophobic surface and contribute to its surface charge. The charge density of an ion determines its level of hydration and therefore also its hydrophobicity (Figure 1). It was shown experimentally that the rank order of effectiveness of the anions in salting-out benzene is indeed  $\text{SO}_4^{2-} > \text{Cl}^- > \text{Br}^- > \text{NO}_3^- > \text{I}^-$ , and the rank order of the cations is  $\text{Ca}^{2+} > \text{Na}^+ > \text{K}^+ > \text{NH}_4^+ > \text{Cs}^+$ , which is in agreement with the series in Figure 1.<sup>2,10,66</sup> This corresponds to the Hofmeister series with a reversed cation series because the Hofmeister series was established for the negatively charged hydrophobic protein ovalbumin. Therefore adsorbed cations diminish the surface charge of the protein and lower its solubility. Schwiertz *et al.*, used this to predict the order of the salting-in/salting-out series depending on the surface charge and the hydrophobicity of a protein or colloid surface.<sup>5-6</sup>



**Figure 1.** Salting-in/salting-out series for uncharged molecular solvents and ionic liquids. This ranking of anions and cations follows the hydrophobicity which is a consequence of the charge density and the resulting size of their hydration mantle.

The same order also applies to the solubility of ionic liquids in the water phase.<sup>47,50-54,67-68</sup> However, ILs are more complicated than the abovementioned organic solvents in the sense that they consist of ions themselves. Therefore salts can also cause other effects such as anion exchange, which can negatively affect the ionic liquid. This paper gives an overview of all the effects of metal salts and mineral acids on a selection of biphasic IL/water systems, relevant to solvent extraction. These effects include anion exchange, changes in mutual solubility and effects on the cloud point temperature of thermomorphic systems. The countless different combinations of anions and cations to form ILs, increases the need for a general prediction model that is applicable for all ILs, regardless of the structural characteristics of their anions and cations. Rationalizations and prediction models are therefore provided, which are generally applicable to all water-immiscible ILs. Understanding these aspects is important for the design of stable solvent extraction systems and to minimize the loss of IL to the water phase.<sup>37,46,61,69-77</sup> Particular emphasis was placed on water-immiscible ILs used as organic phase in solvent extraction of metal ions, such as the alkylated ammonium and phosphonium ILs and the functionalized ILs like [Hbet][Tf<sub>2</sub>N].<sup>59-62,73,76,78-79</sup>

## **Experimental**

### **Chemicals**

MgCl<sub>2</sub>·6H<sub>2</sub>O (98%), NaCl (98%), NaClO<sub>4</sub>·H<sub>2</sub>O (98%), NaF (99%), Mg(NO<sub>3</sub>)<sub>2</sub>·6H<sub>2</sub>O, KSCN (99%), LiNO<sub>3</sub> (99%) and D<sub>2</sub>O (99.9 atom% D) were obtained from Sigma-Aldrich (Diegem, Belgium). CaCl<sub>2</sub>·2H<sub>2</sub>O (99.5%), NaNO<sub>3</sub> (99%), Na<sub>2</sub>SO<sub>4</sub> (99%), Ca(NO<sub>3</sub>)<sub>2</sub>·4H<sub>2</sub>O (99%), KNO<sub>3</sub> (99%), NH<sub>4</sub>NO<sub>3</sub> (99%) and HNO<sub>3</sub> (65%) were purchased from Chem-Lab (Zedelgem, Belgium). KCl (99.5%) and NaI (99.5%) were purchased from AppliChem (Darmstadt, Germany) and LiCl

(99%) from Fisher Chemical (Loughborough, UK). CsCl (99%), NaBr (99.5%), NH<sub>4</sub>Cl (99.5%), H<sub>2</sub>SO<sub>4</sub> (96%), HClO<sub>4</sub> (70%), HCl (37%) and 1,4-dioxane (99.9%) were obtained from Acros Organics (Geel, Belgium). The silicone solution in isopropanol was purchased from SERVA Electrophoresis GmbH (Heidelberg, Germany). All chemicals were used as received without further purification.

### Ionic liquids

Table 1 shows the ILs used in this work. An overview of the chemical structure of all the ILs is provided in the supplementary information (Figure S2). The ILs [N<sub>4111</sub>][Tf<sub>2</sub>N] (99%), [S<sub>222</sub>][Tf<sub>2</sub>N] (99%), [Chol][Tf<sub>2</sub>N] (99%), [emim][Tf<sub>2</sub>N] (99%) and [mppip][Tf<sub>2</sub>N] (99%) were purchased from IoLiTec (HeilBronn, Germany). The ILs [P<sub>8444</sub>][Cl] (Cyphos<sup>®</sup> 253), [P<sub>66614</sub>][Cl] (Cyphos<sup>®</sup> 101) and [P<sub>66614</sub>][Br] (Cyphos<sup>®</sup> 102) were purchased from Cytec (Vlaardingen, Netherlands) and [N<sub>8881</sub>][Cl] (Aliquat<sup>®</sup> 336) was obtained from Sigma-Aldrich (Diegem, Belgium). The commercially available ILs were used as received without further purification. For the synthesized ILs, a detailed overview of the synthesis procedures and required chemicals is given in the supplementary information.

**Table 1.** Overview of the ionic liquids used in this work.

Formula	Full name	Origin
[P <sub>8444</sub> ][Cl]	tributyl(octyl)phosphonium chloride	Purchased
[P <sub>8444</sub> ][Br]	tributyl(octyl)phosphonium bromide	Synthesized
[P <sub>8444</sub> ][NO <sub>3</sub> ]	tributyl(octyl)phosphonium nitrate	Synthesized
[P <sub>8444</sub> ][ClO <sub>4</sub> ]	tributyl(octyl)phosphonium perchlorate	Synthesized

[P <sub>8444</sub> ][Tf <sub>2</sub> N]	tributyl(octyl)phosphonium bistriflimide <sup>(a)</sup>	Synthesized
[P <sub>66614</sub> ][Cl]	triethyl(tetradecyl)phosphonium chloride	Purchased
[P <sub>66614</sub> ][Br]	triethyl(tetradecyl)phosphonium bromide	Purchased
[P <sub>66614</sub> ][NO <sub>3</sub> ]	triethyl(tetradecyl)phosphonium nitrate	Synthesized
[P <sub>66614</sub> ][Tf <sub>2</sub> N]	triethyl(tetradecyl)phosphonium bistriflimide	Synthesized
[N <sub>8881</sub> ][Cl]	trioctyl(methyl)ammonium chloride	Purchased
[N <sub>4111</sub> ][Tf <sub>2</sub> N]	trimethyl(butyl)ammonium bistriflimide	Purchased
[S <sub>222</sub> ][Tf <sub>2</sub> N]	triethylsulfonium bistriflimide	Purchased
[Hbet][Tf <sub>2</sub> N]	betainium bistriflimide	Synthesized
[Chol][Tf <sub>2</sub> N]	choline bistriflimide	Purchased
[P <sub>444E3</sub> ][DEHP]	tributyl(2-[2-(2-methoxyethoxy)ethoxy]ethyl) phosphonium bis(2-ethylhexyl)phosphate	Synthesized
[P <sub>4441COOH</sub> ][Cl]	tributyl(carboxymethyl)phosphonium chloride	Synthesized
[emim][Tf <sub>2</sub> N]	1-ethyl-3-methylimidazolium bistriflimide	Purchased
[mppip][Tf <sub>2</sub> N]	1-methyl-1-propylpiperidinium bistriflimide	Purchased

---

(a) bistriflimide = bis(trifluoromethylsulfonyl)imide

### Equipment and characterization

<sup>1</sup>H and <sup>13</sup>C spectra were recorded on a Bruker Avance 300 spectrometer, operating at 300 MHz for <sup>1</sup>H and 75 MHz for <sup>13</sup>C. A TMS-200 thermoshaker (Nemus Life) was used to shake the samples and a Heraeus Megafuge 1.0 centrifuge was used to accelerate phase separation. Total reflection X-ray fluorescence (TXRF) analysis was performed with a Bruker S2 Picofox TXRF spectrometer equipped with a molybdenum source. For the sample preparation, plastic microtubes were filled with a small amount of IL sample (10–50 mg) and ethanol/water (700 μL). The microtubes were then vigorously shaken on a vibrating plate (IKA MS 3 basic). Finally, a 1 μL drop of this solution was put on a quartz plate, previously treated with a silicone/isopropanol solution (Serva<sup>®</sup>) to avoid

spreading of the sample droplet on the quartz plate. The quartz plates were then dried for 30 min at 60 °C prior to analysis. Each sample was measured for 5 min.

### **Determination of the IL solubility in the water phase with quantitative $^1\text{H}$ NMR.**

The IL (1 g) was contacted with a water phase (1 g) and shaken for 1 h (25 °C, 2000 rpm) to guarantee equilibrium. The samples were then centrifuged (5000 rpm, 10 min) to accelerate phase separation. A sample of the water phase was taken (100 mg) and mixed with a known amount of 1,4-dioxane (5 mg) and diluted with deuterated water (500 mg). This mixture was then shaken on a vibrating plate (IKA MS 3 basic) and measured with  $^1\text{H}$  NMR. The integrated intensity of the 1,4-dioxane signal ( $\delta = 3.6$ ) was compared with the IL signals (and corrected for the amount of protons) in order to quantify the concentration of IL in the water phase. The water peak did not cause problematic interferences. This analytical was validated using known amounts of betaine in solution (Figure S1) and has an average uncertainty of  $\pm 0.1$  wt%.

### **Determination of the cloud point temperature**

The cloud point temperature ( $T_{\text{CP}}$ ) of thermomorphic IL/water systems was determined visually. An oil bath set-up was used to control the temperature of the IL-containing vial (4 mL) and a temperature probe was present in the mixture. The IL-water solvent mixtures were prepared in a 1:1 wt/wt ratio. The temperature of the sample was gradually increased or decreased (in steps of 0.1 °C) and allowed to equilibrate at every step until phase separation was observed. At every step the sample was shortly agitated (1 s) to overcome a possible metastable state. The determination of the cloud point temperature was repeated three times to guarantee its accuracy.



## **Studying anion exchange with TXRF analysis**

ILs of the type  $[P_{66614}][X_A]$  ( $X_A$  = different anion) (1 g) were contacted with aqueous solutions (1 g) containing 2 equivalents of sodium salts with the desired anion  $X_B$ . The mixtures were shaken (2000 rpm) at 50 °C for 1 h. Then, the samples were centrifuged (5000 rpm) to accelerate phase separation. A sample of the IL phase was then taken to determine the degree of anion exchange. This was quantified by measuring the P/X (phosphor/anion) ratio before and after the exchange, using total reflection X-ray fluorescence (TXRF). These relative measurements did not require an internal standard.

## **Results and discussion**

### **1. Ionic liquid anion exchange**

When a hydrophobic (water-immiscible) IL is contacted with a water phase, a biphasic system is created. If salts are present in the aqueous phase, the salt anions can exchange with the anions of the IL depending on their affinity for the water phase and the IL phase. In some cases anion exchange is intended, for example to synthesize an IL with a different anion than the anion present in the commercial IL.<sup>73</sup> In other cases anion exchange can be an unwanted effect, for example in metal extraction processes with different anions in the IL phase and the water phase. In such processes anion exchange can significantly pollute the IL phase and change its properties. Fortunately, the occurrence of anion exchange can be predicted based on the Hofmeister series. Hydrophobic anions (with low charge density) such as  $Tf_2N^-$ ,  $SCN^-$ ,  $ClO_4^-$  and  $I^-$  prefer to be in the IL, while more hydrophilic anions such as  $Cl^-$  and  $SO_4^{2-}$  prefer to be in the water phase where they are better solvated (Figure 1). The exact order of anion exchange was tested using trihexyl(tetradecyl)phosphonium ILs with the formula  $[P_{66614}][X]$  ( $X = Tf_2N^-$ ,  $NO_3^-$ ,  $Br^-$  and  $Cl^-$ ).

This IL has been used successfully for the extraction of various metal ions.<sup>75-76,78-80</sup> These very hydrophobic ILs were contacted with an aqueous phase (1:1 ratio wt/wt) containing 2 mol equivalents of a salt (LiTf<sub>2</sub>N, NaSCN, NaClO<sub>4</sub>, NaI, NaNO<sub>3</sub>, NaBr, NaCl, Na<sub>2</sub>SO<sub>4</sub>). The mixtures were shaken (2000 rpm) for 1 h at 50 °C. The P/X ratio (phosphor/anion) in the IL phase was analyzed by TXRF and compared with the initial P/X ratio to obtain the degree of anion exchange (%) (Table 2). The aim was not to obtain full equilibrium, but to measure the relative tendency of salt anions to exchange with IL anions.

**Table 2.** Degree of anion exchange (%) after contacting several ILs with salt-containing aqueous solutions (2 equivalents).<sup>(a)</sup> The mixtures were shaken (2000 rpm) for 1 h at 50 °C. The anion exchange was quantified by TXRF.

	Tf <sub>2</sub> N <sup>-</sup>	SCN <sup>-</sup>	ClO <sub>4</sub> <sup>-</sup>	I <sup>-</sup>	NO <sub>3</sub> <sup>-</sup>	Br <sup>-</sup>	Cl <sup>-</sup>	SO <sub>4</sub> <sup>2-</sup>
[P <sub>66614</sub> ][Tf <sub>2</sub> N]	(b)	(b)	2.9	0.4	0.1	0.04	0.01	<DL <sup>(c)</sup>
[P <sub>66614</sub> ][NO <sub>3</sub> ]	98.7	98.1	97.3	96.9	(b)	51.2	16.4	0.5
[P <sub>66614</sub> ][Br]	99.7	99.5	99.4	99.1	84	(b)	27.1	1.8
[P <sub>66614</sub> ][Cl]	100	100	(b)	99.9	97.6	96.1	(b)	2.5


(a) Sodium salts were used except for LiTf<sub>2</sub>N and KSCN.

(b) Not quantifiable because the same element is present after exchange

(c) Below the detection limit for TXRF (1 ppm)

Anion exchange is increasingly efficient from right to left (Table 2): SO<sub>4</sub><sup>2-</sup> < Cl<sup>-</sup> < Br<sup>-</sup> < NO<sub>3</sub><sup>-</sup> < I<sup>-</sup> < ClO<sub>4</sub><sup>-</sup> < SCN<sup>-</sup> < Tf<sub>2</sub>N<sup>-</sup>, which corresponds to a decrease in charge density (Figure 1). Ions with a lower charge density are less well hydrated and have a higher affinity for the IL phase. The efficiency of anion exchange is also dependent on the IL anion (in the opposite direction). ILs

containing  $\text{Tf}_2\text{N}^-$  anions are very difficult to exchange, while chloride ILs are very easy to exchange (Table 2). This is summarized in a graphical overview (Figure 2). The anions considered in this work are derived from strong acids and are therefore fully deprotonated at neutral pH. Note however that for anions derived from weak acids, their speciation will be pH dependent. This has to be taken into account as it will also influence their tendency for anion exchange.

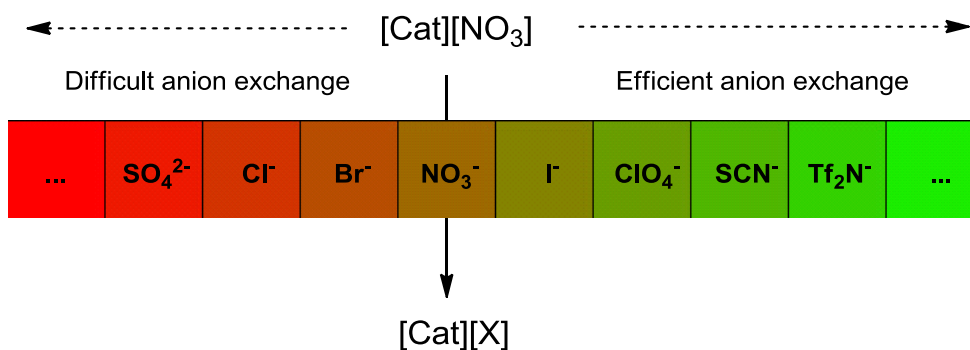

**Figure 2.** Prediction tool for the occurrence of anion exchange when a hydrophobic IL is contacted with a salt-containing water phase. The tendency of an IL  $[\text{Cat}][\text{X}_A]$  towards anion exchange with a salt  $\text{MX}_B$  is shown. For example for an IL  $[\text{Cat}][\text{NO}_3]$ , the exchange will be efficient with the anions to the right, and difficult with the anions to the left of the position of  $\text{NO}_3^-$  in the series. This should be considered when designing IL synthesis routes and extraction systems.

This scheme can be used as a prediction tool for anion exchange which is relevant both for the synthesis of ILs and the design of stable IL/water extraction systems. It is for instance possible to synthesize  $[\text{P}_{66614}][\text{Tf}_2\text{N}]$  in one step starting from  $[\text{P}_{66614}][\text{Cl}]$  and contacting it with an aqueous  $\text{LiTf}_2\text{N}$  solution. The anion exchange reaction is fast and complete. On the other hand the synthesis of  $[\text{P}_{66614}][\text{NO}_3]$  starting from  $[\text{P}_{66614}][\text{Cl}]$  requires three steps to obtain more than 99.9% purity.<sup>73</sup>

For extraction experiments this is also important when a different anion is present in the water phase and the organic or IL phase.<sup>59,61-62,81-82</sup> For example, Vander Hoogerstraete and Onghena *et al.* have reported on metal extraction systems from chloride aqueous solutions using the IL [Hbet][Tf<sub>2</sub>N].<sup>60-62</sup> No chloride ions were detected in the IL since the exchange of Tf<sub>2</sub>N<sup>-</sup> by Cl<sup>-</sup> ions does not occur (Table 2).<sup>59</sup> However, other extraction systems such as the extraction of metal ions from an aqueous phase with [P<sub>66614</sub>][Cl] must be done from chloride solutions to avoid contamination of the IL.<sup>78</sup> Many more examples could be cited, but the conclusion is that due to the endless variety of ILs it is most important to understand the trends in anion exchange (Figure 2), so that an appropriate and stable extraction system can be designed for any given IL. Cation exchange is not observed since small inorganic cations do not form ILs and are always more hydrophilic than the bulky organic IL cations.

## **2. Water-miscibility of ionic liquids: structure dependence**

An important parameter in solvent extraction is the solubility of the organic phase in the aqueous phase. This can cause pollution of the water and loss of (valuable) organic solvent. In the case of IL/water extraction systems this is particularly important due to their high cost. Recovery of ILs from water with physical methods such as nanofiltration or electrodialysis is still relatively cumbersome.<sup>83-86</sup> Therefore, it is more practical to limit the loss of IL to the aqueous phase in the first place by altering the structure of the IL or by the addition of metal salts to the aqueous phase.<sup>69</sup> The inherent solubility of the IL in the aqueous phase can vary a lot depending on the IL structure and the polarity of its anions and cations.<sup>87</sup> The long-chain tetraalkylphosphonium IL [P<sub>66614</sub>][Cl] for example, has a very low water solubility of 20–80 ppm (0.002–0.008 wt%), while the carboxyl-functionalized IL [Hbet][Tf<sub>2</sub>N] has a water solubility of 14 wt%.<sup>59,80</sup> A straightforward way to

alter the water-miscibility of a certain IL, is by changing the IL cation or IL anion. The effect of the anion (X) on the water solubility is shown for the IL [P<sub>8444</sub>][X] (Table 3) and the effect of cation (Cat) is shown for the IL [Cat][Tf<sub>2</sub>N] (

Table 4). The trends can be of interest when choosing an IL for solvent extraction.

**Table 3.** Solubility of the IL [P<sub>8444</sub>][X] in the water phase at 25 °C, for increasingly hydrophobic anions X. A 1:1 ratio (wt/wt) of IL/water was used.

	Ionic liquid content in the water phase (wt%) <sup>(a)</sup>
[P <sub>8444</sub> ][Cl]	Homogeneous system
[P <sub>8444</sub> ][Br]	2.14
[P <sub>8444</sub> ][NO <sub>3</sub> ]	0.91
[P <sub>8444</sub> ][ClO <sub>4</sub> ]	0.04
[P <sub>8444</sub> ][Tf <sub>2</sub> N]	< DL <sup>(b)</sup>

(a) All IL/water systems were biphasic, except for [P<sub>8444</sub>][Cl]. [P<sub>8444</sub>][Br] has thermomorphic behavior with a LCST (24 °C) but is biphasic at 25 °C.<sup>88</sup>

(b) Below detection limit using quantitative <sup>1</sup>H NMR.

**Table 4.** Solubility (25 °C) of the ILs [Cat][Tf<sub>2</sub>N] in the water phase for increasingly hydrophobic cations (Cat) and 1:1 IL/water ratio wt/wt.

	Ionic liquid content in the water phase (wt%) <sup>(a)</sup>
[Hbet][Tf <sub>2</sub> N]	14.0
[Chol][Tf <sub>2</sub> N]	10.7
[N <sub>4111</sub> ][Tf <sub>2</sub> N]	1.1

[S <sub>222</sub> ][Tf <sub>2</sub> N]	0.81
[emim][Tf <sub>2</sub> N]	0.72
[mppip][Tf <sub>2</sub> N]	0.14
[N <sub>8881</sub> ][Tf <sub>2</sub> N]	< DL
[P <sub>66614</sub> ][Tf <sub>2</sub> N]	< DL (Literature value: 0.002–0.008 wt%) <sup>80</sup>

---

(a) All IL/water systems were biphasic at 25 °C.

(b) Below detection limit using quantitative <sup>1</sup>H NMR.


For the IL anions (Table 3), the hydrophobicity of the ILs follows the charge density series (Figure 1). Anions can alter the hydrophobicity of the IL very much: [P<sub>8444</sub>][Cl] is water soluble, while [P<sub>8444</sub>][Br] forms a biphasic system with only around 2 wt% of IL in the aqueous phase. These large differences can be used to change the properties of known ILs by simply exchanging the IL anion (Figure 2). For cations, the differences are smaller between structurally similar aliphatic cations. However, when functional groups are incorporated in the cation (e.g. [Hbet]<sup>+</sup> or [Chol]<sup>+</sup>), significantly higher solubilities are observed due to the formation of hydrogen bonds (

Table 4). Water can also dissolve in the IL phase, but this is not problematic since it does not pollute the system nor cause loss of valuable reagents. Note however, that for very hydrophobic ILs such as [C<sub>8</sub>mim][Tf<sub>2</sub>N] or [P<sub>66614</sub>][Tf<sub>2</sub>N], the solubility of water in the IL is significant, while the solubility of IL in the aqueous phase is almost negligible.<sup>67,80</sup>

### 3. Effect of metal salts on the mutual solubility of biphasic IL/water systems

Instead of changing the structure of the IL to influence its water solubility, it is also possible to add metal salts to the aqueous phase. Salts can influence the solubility of ILs in the aqueous phase and improve the process design and recovery of IL in solvent extraction processes.<sup>69</sup> It is therefore


important to understand the effect that the presence of metal salts in aqueous phase can have on the solubility of ILs. The effect of metal salts has been studied for some specific ILs such as  $[\text{C}_4\text{mim}][\text{CF}_3\text{SO}_3]$  and  $[\text{C}_4\text{mim}][\text{Tf}_2\text{N}]$  but there is no general prediction model.<sup>47,50-54,67-68</sup> An intuitive model is therefore proposed here to rationalize the effect of metal salts on the solubility of any hydrophobic IL. In the *liquid-precipitate model* (Figure 3), biphasic IL/water systems are thought of as liquid organic salts (the IL) precipitating out of solution, while maintaining a certain equilibrium concentration in the aqueous phase, similar to the behaviour of solid salt precipitates. Note that nano-aggregates of IL can exist in the aqueous phase, but this does not change the conclusions derived from this model.

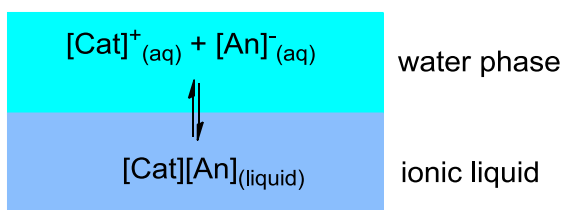

**Figure 3.** Schematic overview of the liquid-precipitate model described in this work. The model is based on the assumption that when a hydrophobic IL is contacted with water it behaves like a liquid-precipitate which is in equilibrium with an amount of dissolved IL in the water phase, just like salt precipitates.


As a consequence, the solubility of the hydrophobic IL is governed by the ability of the aqueous phase to solvate the IL cations and anions and counter the electrostatic attraction between the IL cations and anions. More polar IL anions and cations result in a better solvation by water molecules and therefore a higher water solubility. In the presence of salts, charge-neutralizing ion pairs can be formed between the IL ions and salt counter ions.<sup>31</sup> Salts ions that are more effective at neutralizing the IL ion charge than water molecules, decrease the IL solubility (salting-out). Salt

ions that are less effective at neutralizing the IL ions charge than water molecules, increase the IL solubility (salting-in). Therefore, the effect of salts on the solubility of ILs follows the charge-density series (Figure 1) because a higher charge density results in stronger charge-neutralizing ion pairs.<sup>31</sup> This salting-out series based on the charge density (Figure 1) is valid for every IL regardless of its structure, but its best visible for hydrophobic ILs with a large water solubility (e.g. [Chol][Tf<sub>2</sub>N] and [Hbet][Tf<sub>2</sub>N]). The ILs were contacted with water to form biphasic systems and a range of inorganic salts was then added to the water to reveal the effect of salt cations (Figure 4) and anions (Figure 5) on the solubility of these different ILs. The IL content in the water phase was determined by quantitative <sup>1</sup>H NMR. The results are in agreement with previously published results for ILs such as [C<sub>4</sub>mim][CF<sub>3</sub>SO<sub>3</sub>] and [C<sub>4</sub>mim][Tf<sub>2</sub>N].<sup>47,51</sup> Note that this salting-out series for ILs (Figure 1) is different from the behavior of proteins, colloidal surfaces and polymers, where the effect of salts on the solubility is determined by the ability of adsorbed ions to increase the surface charge and improve the solubility by countering the Van der Waals interactions.<sup>5-8</sup>

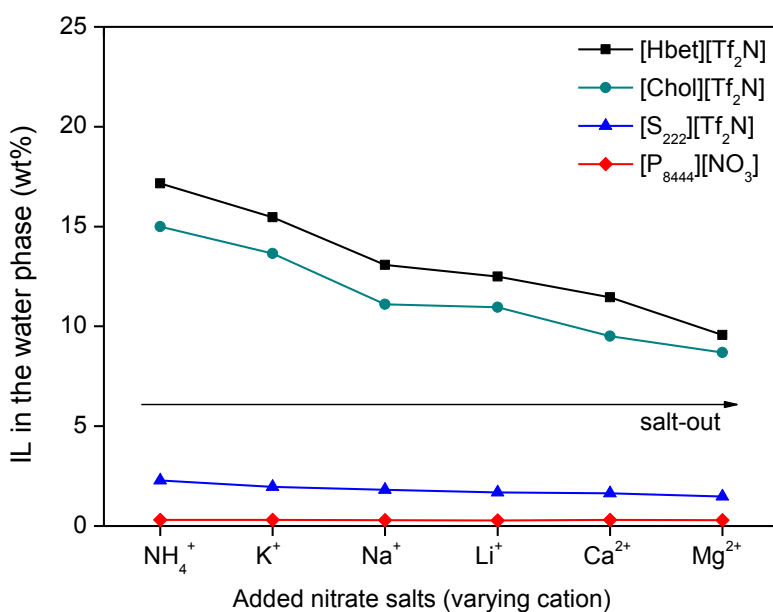




**Figure 4.** Influence of salt cations (added as nitrate salts,  $0.5 \text{ mol.kg}^{-1}$ ) on the solubility of different ILs in the water phase (1:1 wt/wt ratio of IL/ $\text{H}_2\text{O}$ ).

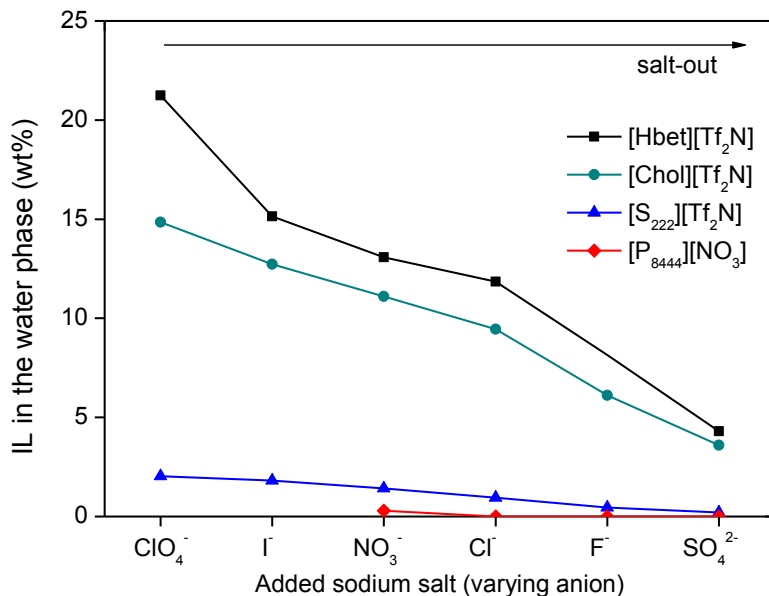


**Figure 5.** Influence of salt anions (added as sodium salts,  $0.5 \text{ mol.kg}^{-1}$ ) on the solubility of different ILs in the water phase (1:1 ratio wt/wt of IL/ $\text{H}_2\text{O}$ ). For  $[\text{P}_{8444}][\text{NO}_3]$ , the anions  $\text{I}^-$  and  $\text{ClO}_4^-$  could not be tested due to anion exchange.

The influence of the salt *concentration* on the salting-in and salting-out effect was also investigated. A higher salt concentration simply reinforces the abovementioned effects on the IL solubility, by increasing the salting-in or salting-out effects compared to pure water. This concentration effect was observed for all investigated ILs but is shown here for  $[\text{Hbet}][\text{Tf}_2\text{N}]$  (Figure 6 and 7). The reason that some data points seem illogical is that the effect of the counter ion has to be taken into account. For example for  $\text{NH}_4^+$  ions (Figure 6), the salting-in effect does increase with the concentration at first, but the increasing  $\text{Cl}^-$  concentration counters this effects at high salt concentrations, due to its salting-out effect (Figure 5). The dominant salting-out effect of

salts at high concentrations is a direct consequence of the abovementioned model. At high salt concentrations the charge neutralizing effect of the salt ions on the IL ions will become more predominant, even for the ions with low charge densities, resulting in a lower IL solubility. This predominant salting-out effect at high salt concentrations was previously also observed by Freire *et al.*<sup>51</sup> Strong salting-out agents have been used previously to successfully recover spent IL from aqueous waste streams.<sup>69,89</sup> For example, [Hbet][Tf<sub>2</sub>N] can be recovered efficiently by addition of Na<sub>2</sub>SO<sub>4</sub> to the IL-containing aqueous phase. A concentration of 3 M Na<sub>2</sub>SO<sub>4</sub> can reduce the [Hbet][Tf<sub>2</sub>N] content in the aqueous phase to less than 0.15 wt%, compared to 14 wt% without salts.<sup>59,89</sup>

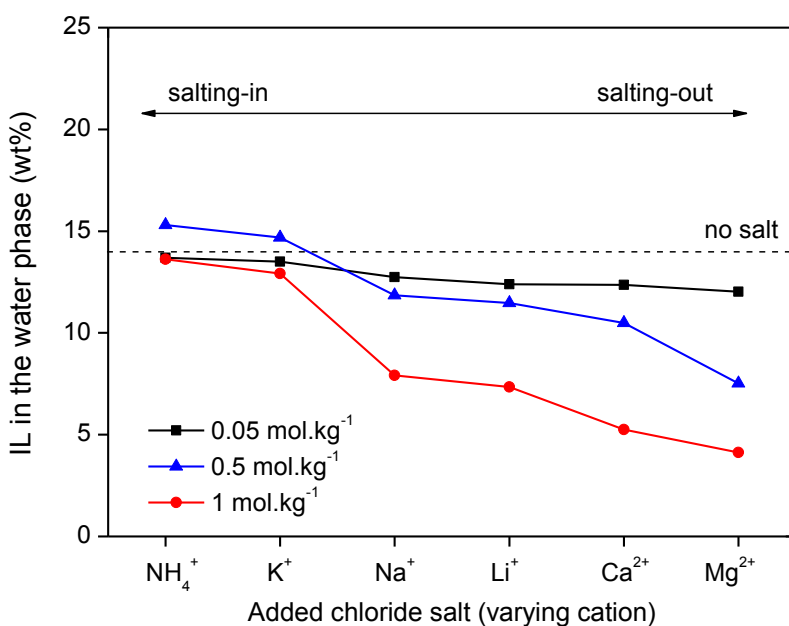


**Figure 6.** [Hbet][Tf<sub>2</sub>N] content (wt%) in the water phase when adding different chloride salts and concentrations. A 1:1 wt/wt ratio of IL/H<sub>2</sub>O was used.

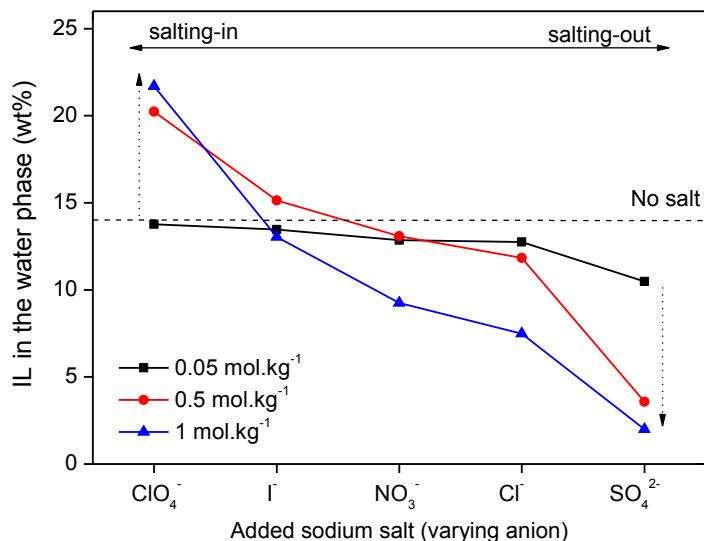

**Figure 7.** *[Hbet][Tf<sub>2</sub>N]* content (wt%) in the water phase when adding different sodium salts and concentrations. A 1:1 wt/wt ratio of IL/H<sub>2</sub>O was used.


#### 4. Effect of mineral acids on the mutual solubility of biphasic IL/water systems.

Extraction systems with acidic extractants require acids to strip the extracted metals. For ILs this is the case when the extracting IL is functionalized with an acidic group such as the carboxyl-functionalized *[Hbet][Tf<sub>2</sub>N]* or when the IL is used as a diluent for an acidic extractant such as the *[Chol][Tf<sub>2</sub>N]*/ *[Chol][hfac]* extraction system (Figure 8).<sup>59-62</sup> In both cases, stripping with acids is required to remove the metals from the IL phase after extraction.<sup>59-62</sup> The addition of concentrated mineral acids can significantly affect the solubility of the IL in the water phase, which can be an issue due to unwanted loss of IL.

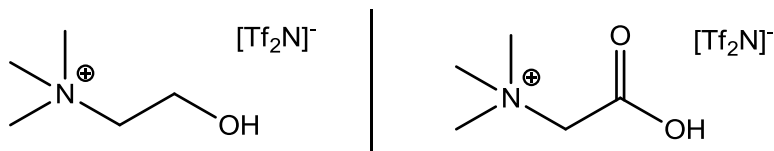

**Figure 8.** Structure of choline bis(trifluoromethylsulfonyl)imide *[Chol][Tf<sub>2</sub>N]* (left) and betainium bis(trifluoromethylsulfonyl)imide *[Hbet][Tf<sub>2</sub>N]* (right).


The ILs were contacted with an aqueous phase containing different mineral acids to investigate the effect on the IL solubility (Figure 9). The results are compared with the effect of equivalent sodium salts. It is clear that mineral acids follow the same salting-out trend ( $\text{H}_2\text{SO}_4 > \text{HCl} > \text{HNO}_3 > \text{HClO}_4$ ) as their salt analogues. However, protons appear to be stronger salting-in agents than expected based on their charge density. This anomaly has been reported previously by Freire *et al.* for other ILs such as  $[\text{C}_4\text{mim}][\text{Tf}_2\text{N}]$  and was attributed to the basic character of the  $\text{Tf}_2\text{N}^-$  anion.<sup>51</sup> The fact that no significant difference was observed between the Brønsted acid functionalized  $[\text{Hbet}][\text{Tf}_2\text{N}]$  and the alcohol functionalized  $[\text{Chol}][\text{Tf}_2\text{N}]$  (Figure 9), supports that hypothesis. Although, the exact origin of the salting-in by acidic protons may not be fully understood yet, it is important to know that it exists because it influences the loss of IL during the stripping process.

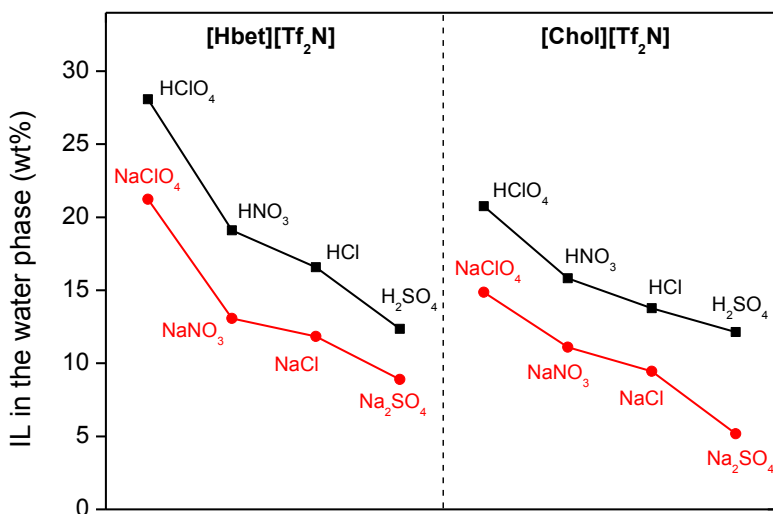

**Figure 9.** IL solubility (wt%) in the aqueous phase (1:1 wt/wt phase ratio) when adding mineral acids (1 N) or sodium salts (1 M). Without additives,  $[\text{Hbet}][\text{Tf}_2\text{N}]$  has a solubility of 14 wt% and  $[\text{Chol}][\text{Tf}_2\text{N}]$  10.7 wt%.

## 5. Effect of metal salts and mineral acids on the cloud point temperature of thermomorphic IL/water systems

A lot of research has been done on the design of ILs with thermomorphic properties.<sup>55,68,88,90-96</sup> Thermomorphic systems change between a homogeneous system and a biphasic system by crossing the cloud point temperature ( $T_{CP}$ ). This can be useful for biphasic extraction systems since a homogeneous phase guarantees very fast extraction equilibrium by removing the phase boundary.<sup>60-62</sup> This is especially true for ILs due to their high viscosity and relatively slow extraction kinetics.<sup>60-62</sup> Two types of thermomorphic systems can be distinguished based on the shape of the phase diagram (Figure 10): systems with an *upper critical solution temperature* (UCST) and systems with a *lower critical solution temperature* (LCST). For UCST systems, the mixture is biphasic below the cloud point temperature ( $T < T_{CP}$ ) and homogeneous above the cloud point temperature ( $T > T_{CP}$ ) and for LCST systems the opposite is observed. The cloud point temperature and thermomorphic properties of an IL/water system can be controlled by altering the composition of the two phases (e.g. add salts) or by changing the phase ratio (Figure 10).<sup>55</sup>

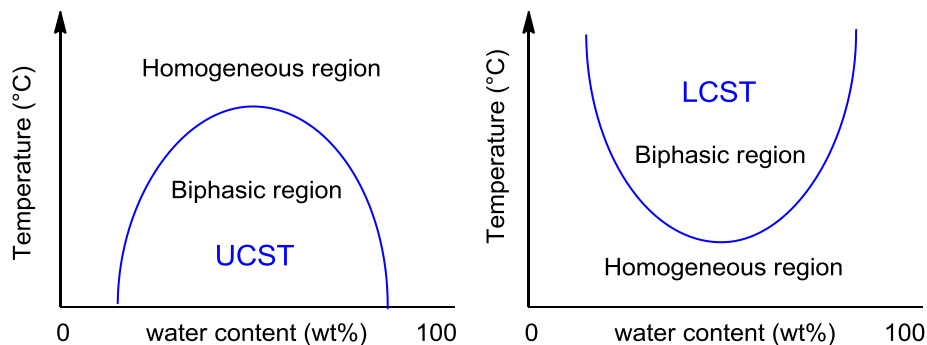

**Figure 10.** Schematic overview of the phase diagram of IL/water systems with an upper critical solution temperature (UCST) and lower critical solution temperature (LCST).

It is well known that for thermomorphic behavior to occur in IL/water systems, the IL must have the right balance between hydrophobic and hydrophilic character.<sup>55,68,88,90-96</sup> However, to the best of our knowledge no general rules exist to predict whether the IL will have UCST or LCST behavior. Some guidelines are introduced here for the rational design of ILs with UCST or LCST behavior, based on the choice of IL anion. Thermodynamically, mixing of two components occurs when the Gibbs free energy of mixing is negative (eq 1).

$$\Delta G_{\text{mix}} = \Delta H_{\text{mix}} - T\Delta S_{\text{mix}} \quad (1)$$

For thermomorphic systems this means that UCST behavior is observed when the entropy of mixing ( $\Delta S_{\text{mix}}$ ) is positive and LCST behavior when  $\Delta S_{\text{mix}}$  is negative. UCST behavior is more common since mixing two components is most likely to increase the entropy of the system ( $\Delta S_{\text{mix}} > 0$ ).<sup>68</sup> LCST is less common than UCST but can occur when  $\Delta S_{\text{mix}}$  is negative. Despite the large variety of anions and cations in ILs, some trends can be observed. Using lists of known thermomorphic IL/water systems such as the one provided by Kohno *et al.*,<sup>88</sup> we derived a general guideline for the rational design of systems with UCST or LCST behavior. It is our observation that generally ILs with weakly-hydrated (low charge density) anions (e.g.  $\text{Tf}_2\text{N}^-$ ,  $\text{BF}_4^-$ ,  $\text{I}^-$ ) show UCST behavior, while ILs with more strongly hydrated (high charge density) anions (e.g.  $\text{Cl}^-$ ,  $\text{Br}^-$ ,  $\text{CF}_3\text{COO}^-$ ) show LCST behavior.<sup>88</sup> This is in agreement with the currently known thermomorphic IL/water systems.<sup>68,88,90-95</sup> The explanation is that ions with a higher charge density, structure a lot of water molecules around them to solvate their charge when dissolved in water. This reduces the entropy of mixing, which can become negative, resulting in LCST behavior. Low charge density ions on the other hand, do not structure much water molecules around them which is why the entropy of mixing is generally positive (UCST behavior). Note how this is again related to the

charge density (Hofmeister) series (Figure 1). A striking example is the contrast between the IL [P<sub>4444</sub>][maleate] (LCST) and [P<sub>4444</sub>][fumarate] (UCST).<sup>91</sup> Fumaric and maleic acid have the same molecular formula but due to their conformation, maleic acid is a hundred times more soluble in water than fumaric acid. This means the hydration of maleic acid is much stronger which explains the LCST behavior according to the abovementioned hypothesis. For biphasic systems consisting of ILs and apolar organic solvents, the affinity of the solvent for the IL anions is opposite to the situation for water. This results in a reversal of the above mentioned rules, because the hydrophobic anions now have a higher affinity for the apolar solvent than hydrophilic anions. An interesting example is the fact that [C<sub>4mim</sub>][PF<sub>6</sub>] and [C<sub>4mim</sub>][Tf<sub>2</sub>N] have UCST behavior in polar solvents and LCST behavior in apolar solvents.<sup>88</sup> An overview of the abovementioned rules for the rational design of ILs with UCST or LCST behavior is shown in


Figure 11.

	<b>weakly-hydrated IL anion</b> (e.g. Tf <sub>2</sub> N <sup>-</sup> , PF <sub>6</sub> <sup>-</sup> , BF <sub>4</sub> <sup>-</sup> )	<b>highly-hydrated IL anion</b> (e.g. Cl <sup>-</sup> , Br <sup>-</sup> , CF <sub>3</sub> COO <sup>-</sup> )
polar solvent	<b>UCST</b>	<b>LCST</b>
apolar solvent	<b>LCST</b>	<b>UCST</b>


**Figure 11.** Prediction model for the rational design of ILs with UCST or LCST behavior. The UCST or LCST behavior of a biphasic IL/solvent system is determined by the charge density (hydration) of the IL anion (Figure 1).

It can be useful to tune the cloud point temperature of a thermomorphic IL/water system, so that the phase transition occurs at the desired temperature. The cloud point temperature is influenced by the IL/water ratio (Figure 10) and by the addition of metal salts.<sup>55,96</sup> The effect of metal salts on the cloud point temperature is different for UCST and LCST systems, but can be rationalized by linking it to the solubility of the IL in the aqueous phase. The addition of salting-in salts improves the mutual solubility of both phases and therefore favors the mixed (homogeneous) state. For UCST systems this means a decrease in the cloud point temperature while for LCST systems this means an increase in the cloud point temperature (Figure 10). Salting-out salts on the other hand, decrease the mutual solubility and therefore promote demixing of the phases which results in an increase of the cloud point temperature for UCST systems and a decrease for LCST systems.<sup>55,97</sup> This is shown here for the LCST system [P<sub>444</sub>E<sub>3</sub>][DEHP]-H<sub>2</sub>O and the UCST system [Hbet][Tf<sub>2</sub>N]-H<sub>2</sub>O. Both ILs are very relevant for solvent extraction.<sup>60,98-99</sup> These systems have a T<sub>CP</sub> of 55 °C and 51 °C respectively, when no salts are added. This opposite effect on the cloud point temperature is clearly visible by comparing the effect of metal salts on the solubility of these two ILs in the water phase (Figure 12), with the change in cloud point temperature (Figure 13) caused by these same salts. It is evident that salt anions have a larger effect than salt cations. This is in agreement with previous observations (Figure 4 and 5) and is due to the poorer solvation of anions in water compared to cations.<sup>100</sup>



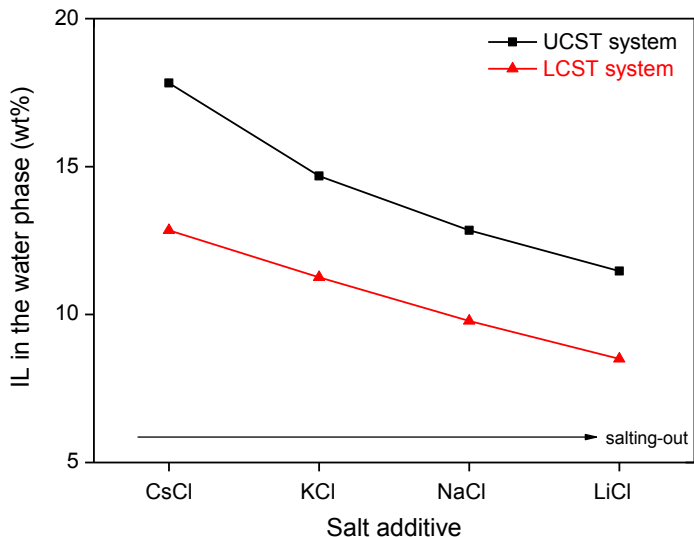

**Figure 12.** Effect of metal salts on the solubility of IL (wt%) in the water phase of the UCST system  $[Hbet][Tf_2N]-H_2O$  (1:1 wt/wt) and the LCST system  $[P_{444}E_3][DEHP]-H_2O$  (1:1 wt/wt). The salt concentration was  $0.5 \text{ mol.kg}^{-1}$  for the UCST system and  $0.1 \text{ mol.kg}^{-1}$  for the LCST system.

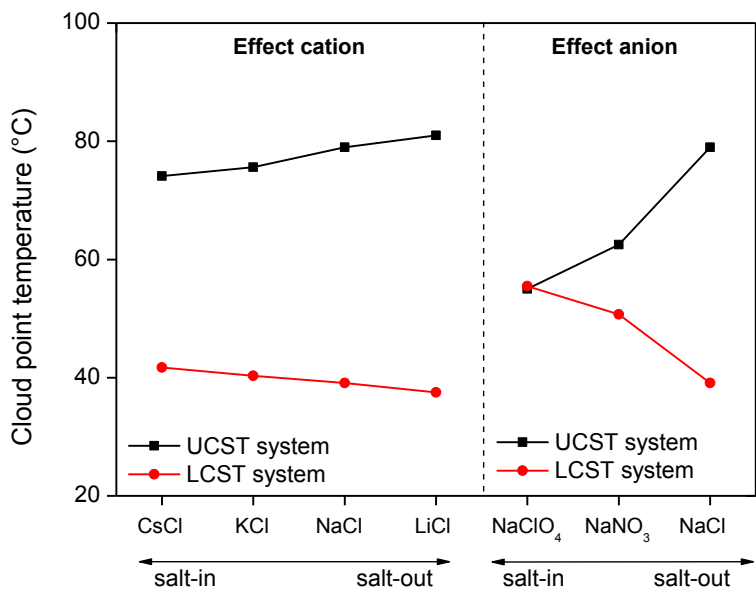

**Figure 13.** Effect of metal salts on the cloud point temperature of thermomorphic IL/water systems (1:1 wt/wt) with an UCST ( $[Hbet][Tf_2N]-H_2O$ ) and an LCST ( $[P_{444}E_3][DEHP]-H_2O$ ). A salt

concentration of  $0.5 \text{ mol.kg}^{-1}$  was used for the UCST system and  $0.1 \text{ mol.kg}^{-1}$  for the LCST system. Without salt, the UCST system has a cloud point of  $55 \text{ }^\circ\text{C}$  and the LCST system of  $51 \text{ }^\circ\text{C}$ .

Finally, the impact of some mineral acids on the cloud point temperature of [Hbet][Tf<sub>2</sub>N]-H<sub>2</sub>O is shown (Table 5). For acidic extractants such as [Hbet][Tf<sub>2</sub>N], acids are required to strip extracted metal ions back to the water phase. It is therefore useful to understand the impact of acids on the cloud point temperature of the system. The trend in TCP is in agreement with the effect of the various acids on the solubility of IL in the water phase (Figure 9).

**Table 5.** Cloud point temperature of a [Hbet][Tf<sub>2</sub>N]-H<sub>2</sub>O system (1:1 wt/wt) when adding different mineral acids (1 N).


	Cloud point temperature ( $^\circ\text{C}$ )
HClO <sub>4</sub>	24.2
HNO <sub>3</sub>	49.4
No acid	55.0
HCl	67.5
H <sub>2</sub> SO <sub>4</sub>	66.5 <sup>(a)</sup>

<sup>(a)</sup>The cloud point for H<sub>2</sub>SO<sub>4</sub> (1 N) is lower than for HCl (1 N) because the concentration of sulfate ions is only half that of chloride ions.

## 6. Effect of metal salts on water-soluble ILs

So far we have discussed hydrophobic (water immiscible) ionic liquids that form biphasic IL/water systems. However, certain hydrophilic (water miscible) ILs can also form biphasic IL/water systems in the presence of large amounts of salt. These so-called Aqueous Biphasic

Systems (ABS) are salt-induced biphasic systems that consist of two components (a hydrophilic IL and water) that are fully miscible in the absence of salts.<sup>34-49</sup> This field has grown very rapidly and is not discussed here in detail as it has been reviewed previously by Freire *et al.*<sup>34</sup> It is however interesting to note that the salting-out effect follows the same trend as the previously discussed IL/water systems and is often even more pronounced due to the large salt concentrations and high water solubility of the ILs used in ABS. We will restrict the discussion to a new carboxyl-functionalized ABS system with LCST behavior that was recently developed in our lab: [P<sub>444</sub>C<sub>1</sub>COOH][Cl]. This ionic liquid is very relevant due to its ability to extract metal ions. As mentioned before, carboxyl-functionalized ILs have been used successfully for metal ion extractions.<sup>59-62</sup> Note that the LCST behavior of this ABS system is also in agreement with our rational design model, which predicts LCST behavior for thermomorphic ILs with chloride anions. The large effect of salts on the cloud point temperature of this thermomorphic IL is shown in Figure 14.

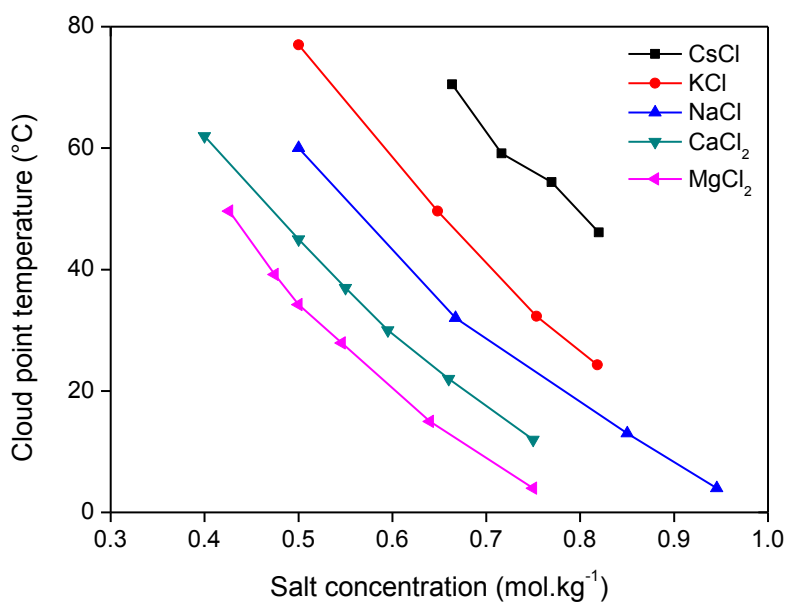

*Figure 14. Effect of salt concentration on the cloud point temperature (LCST) of the aqueous biphasic system [P<sub>444</sub>C<sub>1</sub>COOH][Cl]–H<sub>2</sub>O (1:1 ratio wt/wt).*

## Conclusions

Biphasic IL/water systems show a lot of potential for solvent extraction. However, the presence of metal salts can affect these systems in many different ways such as (un)wanted anion exchange, changes in mutual solubility and changes in cloud point temperature in the case of thermomorphic. Due to the endless variety of ILs it is important to find general trends instead of relying on case-by-case reports. Here, an overview is given of all the effects and intuitive guidelines and models are introduced to predict the effects of metal salts on any given IL/water system. Anion exchange was investigated and translated into guidelines for stable solvent extraction systems and synthetic strategies for ILs. The salting-in/salting-out effect of salts on the miscibility of ILs in water was also discussed and rationalized based on the charge density series (Hofmeister series). Salting-out salts can be used to recover lost IL in the aqueous phase and thus avoid pollution of the water. The effect of metal salts on the cloud point temperature of thermomorphic systems was also investigated. Thermomorphic systems with an upper critical solution temperature (UCST) are affected differently by salts than systems with a lower critical solution temperature (LCST). Finally, new insights were introduced for the rational design of thermomorphic ILs with UCST or LCST behavior. This paper is intended as a tool for the rational design of ILs and (thermomorphic) IL/water extraction systems as well as an overview of the general rules to find the most suitable salt additives. These insights will hopefully give an additional boost to this promising field of IL solvent extraction systems.

## ASSOCIATED CONTENT

**Supporting Information.** Overview of the synthesis procedures, characterization, chemicals and equipment for the synthesized ionic liquids. Validation of quantitative  $^1\text{H}$  NMR as analytical technique. This material is available free of charge via the Internet at <http://pubs.acs.org>.

## AUTHOR INFORMATION

### Corresponding Author

\*K. Binnemans: E-mail: Koen.Binnemans@chem.kuleuven.be

### Notes

The authors declare no competing financial interest.

## ACKNOWLEDGMENT

The authors wish to thank the KU Leuven (projects GOA/13/008 and IOF-KP RARE<sup>3</sup>), the FWO Flanders (PhD fellowship to David Dupont) and the IWT Flanders (PhD fellowship to Daphne Depuydt) for financial support. The authors would like to thank Karel Duerinckx for NMR analysis.

## References

1. Hofmeister, F. Zur Lehre von der Wirkung der Salze. *Arch. Exp. Pathol. Pharmacol.* **1888**, *24*, 247-260.
2. Baldwin, R. L. How Hofmeister Ion Interactions Affect Protein Stability. *Biophys. J.* **1996**, *71*, 2056-2063.

3. Carbonnaux, C.; Ries-Kautt, M.; Ducruix, A. Relative Effectiveness of Various Anions on the Solubility of Acidic Hypoderma Lineatum Collagenase at pH 7.2. *Protein Sci.* **1995**, *4*, 2123-2128.
4. Salis, A.; Cugia, F.; Parsons, D. F.; Ninham, B. W.; Monduzzi, M. Hofmeister Series Reversal for Lysozyme by Change in pH and Salt Concentration: Insights from Electrophoretic Mobility Measurements. *Phys. Chem. Chem. Phys.* **2012**, *14*, 4343-4346.
5. Schwierz, N.; Horinek, D.; Netz, R. R. Reversed Anionic Hofmeister Series: The Interplay of Surface Charge and Surface Polarity. *Langmuir* **2010**, *26*, 7370-7379.
6. Schwierz, N.; Horinek, D.; Netz, R. R. Anionic and Cationic Hofmeister Effects on Hydrophobic and Hydrophilic Surfaces. *Langmuir* **2013**, *29*, 2602-2614.
7. Zhang, Y.; Cremer, P. S. Interactions Between Macromolecules and Ions: the Hofmeister Series. *Curr. Opin. Chem. Biol.* **2006**, *10*, 658-663.
8. Zhang, Y.; Cremer, P. S. The Inverse and Direct Hofmeister Series for Lysozyme. *P. Natl. Acad. Sci. U. S. A.* **2009**, *106*, 15249-15253.
9. Lo Nostro, P.; Ninham, B. W. Hofmeister Phenomena: An Update on Ion Specificity in Biology. *Chem. Rev.* **2012**, *112*, 2286-2322.
10. Pegram, L. M.; Record, M. T. Thermodynamic Origin of Hofmeister Ion Effects. *J. Phys. Chem. B* **2008**, *112*, 9428-9436.
11. Kim, H.; Lee, H.; Lee, G.; Kim, H.; Cho, M. Hofmeister Anionic Effects on Hydration Electric Fields Around Water and Peptide. *J. Chem. Phys.* **2012**, *136*, 124501.
12. Schwartz, C. P.; Uejio, J. S.; Duffin, A. M.; England, A. H.; Kelly, D. N.; Prendergast, D.; Saykally, R. J. Investigation of Protein Conformation and Interactions with Salts via X-ray Absorption Spectroscopy. *P. Natl. Acad. Sci. U. S. A.* **2010**, *107*, 14008-14013.
13. Prevys, V. A.; Wang, B. C.; Spontak, R. J. Effect of Added Salt on the Stability of Hydrogen-Bonded Interpolymer Complexes. *Colloid Polym. Sci.* **1996**, *274*, 532-539.
14. Tomé, L. I. N.; Pinho, S. P.; Jorge, M.; Gomes, J. R. B.; Coutinho, J. A. P. Salting-in with a Salting-out Agent: Explaining the Cation Specific Effects on the Aqueous Solubility of Amino Acids. *J. Phys. Chem. B* **2013**, *117*, 6116-6128.
15. Thormann, E. On Understanding of the Hofmeister Effect: How Addition of Salt Alters the Stability of Temperature Responsive Polymers in Aqueous Solutions. *RSC Adv.* **2012**, *2*, 8297-8305.

16. Wang, J.; Satoh, M. Novel PVA-Based Polymers Showing an Anti-Hofmeister Series Property. *Polymer* **2009**, *50*, 3680-3685.
17. Guo, Y.; Li, S.; Li, W.; Moosa, B.; Khashab, N. M. The Hofmeister Effect on Nanodiamonds: How Addition of Ions Provides Superior Drug Loading Platforms. *Biomater. Sci.* **2014**, *2*, 84-88.
18. Bae, S.; Son, H.; Kim, Y.-G.; Hohng, S. Z-DNA Stabilization is Dominated by the Hofmeister Effect. *Phys. Chem. Chem. Phys.* **2013**, *15*, 15829-15832.
19. Blachechen, L.; Silva, J.; Barbosa, L. S.; Itri, R.; Petri, D. S. Hofmeister Effects on the Colloidal Stability of Poly(Ethylene Glycol)-Decorated Nanoparticles. *Colloid Polym. Sci.* **2012**, *290*, 1537-1546.
20. Zhang, F.; Skoda, M. W. A.; Jacobs, R. M. J.; Dressen, D. G.; Martin, R. A.; Martin, C. M.; Clark, G. F.; Lamkemeyer, T.; Schreiber, F. Gold Nanoparticles Decorated with Oligo(Ethylene Glycol) Thiols: Enhanced Hofmeister Effects in Colloid-Protein Mixtures. *J. Phys. Chem. C* **2009**, *113*, 4839-4847.
21. López-León, T.; Santander-Ortega, M. J.; Ortega-Vinuesa, J. L.; Bastos-González, D. Hofmeister Effects in Colloidal Systems: Influence of the Surface Nature. *J. Phys. Chem. C* **2008**, *112*, 16060-16069.
22. Salis, A.; Ninham, B. W. Models and Mechanisms of Hofmeister Effects in Electrolyte Solutions, and Colloid and Protein Systems Revisited. *Chem. Soc. Rev.* **2014**, *43*, 7358-7377.
23. Wilson, E. K. Hofmeister Still Mystifies. *Chem. Eng. News* **2012**, *90*, 42-43.
24. Kunz, W.; Henle, J.; Ninham, B. W. 'Zur Lehre von der Wirkung der Salze' (About the Science of the Effect of Salts): Franz Hofmeister's Historical Papers. *Curr. Opin. Colloid Interface Sci.* **2004**, *9*, 19-37.
25. Jungwirth, P.; Cremer, P. S. Beyond Hofmeister. *Nature Chem.* **2014**, *6*, 261-263.
26. Leberman, R.; Soper, A. K. Effect of High Salt Concentrations on Water Structure. *Nature* **1995**, *378*, 364-366.
27. Collins, K. D.; Washabaugh, M. W. The Hofmeister Effect and the Behaviour of Water at Interfaces. *Q. Rev. Biophys.* **1985**, *18*, 323-422.
28. Cacace, M. G.; Landau, E. M.; Ramsden, J. J. The Hofmeister Series: Salt and Solvent Effects on Interfacial Phenomena. *Q. Rev. Biophys.* **1997**, *30*, 241-277.

29. Kunz, W.; Lo Nostro, P.; Ninham, B. W. The Present State of Affairs with Hofmeister Effects. *Curr. Opin. Colloid Interface Sci.* **2004**, *9*, 1-18.
30. Gurau, M. C.; Lim, S.-M.; Castellana, E. T.; Albertorio, F.; Kataoka, S.; Cremer, P. S. On the Mechanism of the Hofmeister Effect. *J. Am. Chem. Soc.* **2004**, *126*, 10522-10523.
31. Lyklema, J. Simple Hofmeister series. *Chem. Phys. Lett.* **2009**, *467*, 217-222.
32. Nucci, N. V.; Vanderkooi, J. M. Effects of Salts of the Hofmeister Series on the Hydrogen Bond Network of Water. *J. Mol. Liq.* **2008**, *143*, 160-170.
33. Galamba, N. Mapping Structural Perturbations of Water in Ionic Solutions. *J. Phys. Chem. B* **2012**, *116*, 5242-5250.
34. Freire, M. G.; Claudio, A. F. M.; Araujo, J. M. M.; Coutinho, J. A. P.; Marrucho, I. M.; Lopes, J. N. C.; Rebelo, L. P. N. Aqueous Biphasic Systems: a Boost Brought About by Using Ionic Liquids. *Chem. Soc. Rev.* **2012**, *41*, 4966-4995.
35. Bridges, N. J.; Rogers, R. D. Can Kosmotropic Salt/Chaotropic Ionic Liquid (Salt/Salt Aqueous Biphasic Systems) be Used to Remove Perchnetate From Complex Salt Waste? *Sep. Sci. Technol.* **2008**, *43*, 1083-1090.
36. Pereira, J. F. B.; Rebelo, L. P. N.; Rogers, R. D.; Coutinho, J. A. P.; Freire, M. G. Combining Ionic Liquids and Polyethylene Glycols to Boost the Hydrophobic-Hydrophilic Range of Aqueous Biphasic Systems. *Phys. Chem. Chem. Phys.* **2013**, *15*, 19580-19583.
37. Gutowski, K. E.; Broker, G. A.; Willauer, H. D.; Huddleston, J. G.; Swatloski, R. P.; Holbrey, J. D.; Rogers, R. D. Controlling the Aqueous Miscibility of Ionic Liquids: Aqueous Biphasic Systems of Water-Miscible Ionic Liquids and Water-Structuring Salts for Recycle, Metathesis, and Separations. *J. Am. Chem. Soc.* **2003**, *125*, 6632-6633.
38. Ventura, S. P. M.; Neves, C. M. S. S.; Freire, M. G.; Marrucho, I. M.; Oliveira, J.; Coutinho, J. A. P. Evaluation of Anion Influence on the Formation and Extraction Capacity of Ionic-Liquid-Based Aqueous Biphasic Systems. *J. Phys. Chem. B* **2009**, *113*, 9304-9310.
39. Neves, C. M. S. S.; Ventura, S. P. M.; Freire, M. G.; Marrucho, I. M.; Coutinho, J. A. P. Evaluation of Cation Influence on the Formation and Extraction Capability of Ionic-Liquid-Based Aqueous Biphasic Systems. *J. Phys. Chem. B* **2009**, *113*, 5194-5199.
40. Tomé, L. I. N.; Pereira, J. F. B.; Rogers, R. D.; Freire, M. G.; Gomes, J. R. B.; Coutinho, J. A. P. Evidence for the Interactions Occurring Between Ionic Liquids and Tetraethylene Glycol in Binary Mixtures and Aqueous Biphasic Systems. *J. Phys. Chem. B* **2014**, *118*, 4615-4629.



41. Freire, M. G.; Pereira, J. F. B.; Francisco, M.; Rodríguez, H.; Rebelo, L. P. N.; Rogers, R. D.; Coutinho, J. A. P. Insight into the Interactions That Control the Phase Behaviour of New Aqueous Biphasic Systems Composed of Polyethylene Glycol Polymers and Ionic Liquids. *Chem-Eur. J.* **2012**, *18*, 1831-1839.
42. Bridges, N. J.; Gutowski, K. E.; Rogers, R. D. Investigation of Aqueous Biphasic Systems Formed from Solutions of Chaotropic Salts with Kosmotropic Salts (Salt-Salt ABS). *Green Chem.* **2007**, *9*, 177-183.
43. Ventura, S. P. M.; Sousa, S. G.; Serafim, L. S.; Lima, Á. S.; Freire, M. G.; Coutinho, J. A. P. Ionic Liquid Based Aqueous Biphasic Systems with Controlled pH: The Ionic Liquid Cation Effect. *J. Chem. Eng. Data* **2011**, *56*, 4253-4260.
44. Pereira, J. F. B.; Lima, A. S.; Freire, M. G.; Coutinho, J. A. P. Ionic Liquids as Adjuvants for the Tailored Extraction of Biomolecules in Aqueous Biphasic Systems. *Green Chem.* **2010**, *12*, 1661-1669.
45. Pei, Y.; Wang, J.; Liu, L.; Wu, K.; Zhao, Y. Liquid-Liquid Equilibria of Aqueous Biphasic Systems Containing Selected Imidazolium Ionic Liquids and Salts. *J. Chem. Eng. Data* **2007**, *52*, 2026-2031.
46. Freire, M. G.; Teles, A. R. R.; Canongia Lopes, J. N.; Rebelo, L. P. N.; Marrucho, I. M.; Coutinho, J. A. P. Partition Coefficients of Alkaloids in Biphasic Ionic-Liquid-Aqueous Systems and their Dependence on the Hofmeister Series. *Sep. Sci. Technol.* **2011**, *47*, 284-291.
47. Shahriari, S.; Neves, C. M. S. S.; Freire, M. G.; Coutinho, J. A. P. Role of the Hofmeister Series in the Formation of Ionic-Liquid-Based Aqueous Biphasic Systems. *J. Phys. Chem. B* **2012**, *116*, 7252-7258.
48. Najdanovic-Visak, V.; Lopes, J.; Visak, Z.; Trindade, J.; Rebelo, L. Salting-out in Aqueous Solutions of Ionic Liquids and  $K_3PO_4$ : Aqueous Biphasic Systems and Salt Precipitation. *Int. J. Mol. Sci.* **2007**, *8*, 736-748.
49. Abraham, M. H.; Zissimos, A. M.; Huddleston, J. G.; Willauer, H. D.; Rogers, R. D.; Acree, W. E. Some Novel Liquid Partitioning Systems: Water-Ionic Liquids and Aqueous Biphasic Systems. *Ind. Eng. Chem. Res.* **2003**, *42*, 413-418.
50. Peng, X.-M.; Hu, Y.-F.; Jin, C.-W. Solubilities of Imidazolium-based Ionic Liquids in Aqueous Salt Solutions at 298.15 K. *J. Chem. Thermodyn.* **2011**, *43*, 1174-1177.

51. Freire, M. G.; Carvalho, P. J.; Silva, A. M. S.; Santos, L. M. N. B. F.; Rebelo, L. P. N.; Marrucho, I. M.; Coutinho, J. A. P. Ion Specific Effects on the Mutual Solubilities of Water and Hydrophobic Ionic Liquids. *J. Phys. Chem. B* **2009**, *113*, 202-211.
52. Freire, M. G.; Neves, C. M. S. S.; Carvalho, P. J.; Gardas, R. L.; Fernandes, A. M.; Marrucho, I. M.; Santos, L. M. N. B. F.; Coutinho, J. A. P. Mutual Solubilities of Water and Hydrophobic Ionic Liquids. *J. Phys. Chem. B* **2007**, *111*, 13082-13089.
53. Tomé, L. I. N.; Varanda, F. R.; Freire, M. G.; Marrucho, I. M.; Coutinho, J. A. P. Towards an Understanding of the Mutual Solubilities of Water and Hydrophobic Ionic Liquids in the Presence of Salts: The Anion Effect. *J. Phys. Chem. B* **2009**, *113*, 2815-2825.
54. Freire, M. G.; Santos, L. M. N. B. F.; Fernandes, A. M.; Coutinho, J. A. P.; Marrucho, I. M. An Overview of the Mutual Solubilities of Water–Imidazolium-based Ionic Liquids Systems. *Fluid Phase Equilib.* **2007**, *261*, 449-454.
55. Trindade, J. R.; Visak, Z. P.; Blesic, M.; Marrucho, I. M.; Coutinho, J. A. P.; Canongia Lopes, J. N.; Rebelo, L. P. N. Salting-Out Effects in Aqueous Ionic Liquid Solutions: Cloud-Point Temperature Shifts. *J. Phys. Chem. B* **2007**, *111*, 4737-4741.
56. Sadeghi, R.; Mostafa, B.; Parsi, E.; Shahebrahimi, Y. Toward an Understanding of the Salting-Out Effects in Aqueous Ionic Liquid Solutions: Vapor–Liquid Equilibria, Liquid–Liquid Equilibria, Volumetric, Compressibility, and Conductivity Behavior. *J. Phys. Chem. B* **2010**, *114*, 16528-16541.
57. Zhao, D. Design, Synthesis and Applications of Functionalized Ionic Liquids. PhD Thesis, EPFL, Lausanne, Switzerland, 2007.
58. Plechkova, N. V.; Seddon, K. R. Applications of Ionic Liquids in the Chemical Industry. *Chem. Soc. Rev.* **2008**, *37*, 123-150.
59. Onghena, B.; Binnemans, K. Recovery of Scandium(III) from Aqueous Solutions by Solvent Extraction with the Functionalized Ionic Liquid Betainium Bis(trifluoromethylsulfonyl)imide. *Ind. Eng. Chem. Res.* **2015**, *54*, 1887-1898.
60. Onghena, B.; Jacobs, J.; Van Meervelt, L.; Binnemans, K. Homogeneous Liquid-Liquid Extraction of Neodymium(III) by Choline Hexafluoroacetylacetonate in the Ionic Liquid Choline Bis(trifluoromethylsulfonyl)imide. *Dalton Trans.* **2014**, *43*, 11566-11578.

61. Vander Hoogerstraete, T.; Onghena, B.; Binnemans, K. Homogeneous Liquid–Liquid Extraction of Metal Ions with a Functionalized Ionic Liquid. *J. Phys. Chem. Lett.* **2013**, *4*, 1659-1663.
62. Vander Hoogerstraete, T.; Onghena, B.; Binnemans, K. Homogeneous Liquid–Liquid Extraction of Rare Earths with the Betaine—Betainium Bis(trifluoromethylsulfonyl)imide Ionic Liquid System. *Int. J. Mol. Sci.* **2013**, *14*, 21353-21377.
63. Sasaki, K.; Takao, K.; Suzuki, T.; Mori, T.; Arai, T.; Ikeda, Y. Extraction of Pd(II), Rh(III) and Ru(III) from HNO<sub>3</sub> Aqueous Solution to Betainium Bis(trifluoromethanesulfonyl)imide Ionic Liquid. *Dalton Trans.* **2014**, *43*, 5648-5651.
64. Sasaki, K.; Suzuki, T.; Mori, T.; Arai, T.; Takao, K.; Ikeda, Y. Selective Liquid-Liquid Extraction of Uranyl Species Using Task-specific Ionic Liquid, Betainium Bis(trifluoromethylsulfonyl)imide. *Chem. Lett.* **2014**, *43*, 775-777.
65. Lo, T. C.; Baird, M. H. I.; Hanson, C. *Handbook of Solvent Extraction*. Wiley-Interscience: New York, 1983.
66. Ganguly, P.; Hajari, T.; van der Vegt, N. F. A. Molecular Simulation Study on Hofmeister Cations and the Aqueous Solubility of Benzene. *J. Phys. Chem. B* **2014**, *118*, 5331-5339.
67. Freire, M. G.; Carvalho, P. J.; Gardas, R. L.; Marrucho, I. M.; Santos, L. M. N. B. F.; Coutinho, J. A. P. Mutual Solubilities of Water and the [C<sub>n</sub>mim][Tf<sub>2</sub>N] Hydrophobic Ionic Liquids. *J. Phys. Chem. B* **2008**, *112*, 1604-1610.
68. Kohno, Y.; Ohno, H. Ionic Liquid/Water Mixtures: from Hostility to Conciliation. *Chem. Commun.* **2012**, *48*, 7119-7130.
69. Neves, C. M. S. S.; Freire, M. G.; Coutinho, J. A. P. Improved Recovery of Ionic Liquids from Contaminated Aqueous Streams Using Aluminium-Based Salts. *RSC Adv.* **2012**, *2*, 10882-10890.
70. Li, Z.; Pei, Y.; Wang, H.; Fan, J.; Wang, J. Ionic Liquid-based Aqueous Two-Phase Systems and Their Applications in Green Separation Processes. *Trends Anal. Chem.* **2010**, *29*, 1336-1346.
71. Pei, Y.; Wang, J.; Wu, K.; Xuan, X.; Lu, X. Ionic Liquid-based Aqueous Two-Phase Extraction of Selected Proteins. *Sep. Purif. Technol.* **2009**, *64*, 288-295.

72. Rogers, R. D.; Seddon, K. R. Ionic Liquids--Solvents of the Future? *Science* **2003**, *302*, 792-793.
73. Vander Hoogerstraete, T.; Binnemans, K. Highly Efficient Separation of Rare Earths from Nickel and Cobalt by Solvent Extraction with the Ionic Liquid Trihexyl(tetradecyl)phosphonium Nitrate: a Process Relevant to the Recycling of Rare Earths from Permanent Magnets and Nickel Metal Hydride Batteries. *Green Chem.* **2014**, *16*, 1594-1606.
74. Visser, A. E.; Swatloski, R. P.; Reichert, W. M.; Mayton, R.; Sheff, S.; Wierzbicki, A.; Davis, J. J. H.; Rogers, R. D. Task-Specific Ionic Liquids for the Extraction of Metal Ions from Aqueous Solutions. *Chem. Commun.* **2001**, 135-136.
75. Wellens, S.; Goovaerts, R.; Moller, C.; Luyten, J.; Thijs, B.; Binnemans, K. A Continuous Ionic Liquid Extraction Process for the Separation of Cobalt from Nickel. *Green Chem.* **2013**, *15*, 3160-3164.
76. Wellens, S.; Thijs, B.; Moller, C.; Binnemans, K. Separation of Cobalt and Nickel by Solvent Extraction with Two Mutually Immiscible Ionic Liquids. *Phys. Chem. Chem. Phys.* **2013**, *15*, 9663-9669.
77. Zhang, Q.; Zhang, S.; Deng, Y. Recent Advances in Ionic Liquid Catalysis. *Green Chem.* **2011**, *13*, 2619-2637.
78. Vander Hoogerstraete, T.; Wellens, S.; Verachtert, K.; Binnemans, K. Removal of Transition Metals from Rare earths by Solvent Extraction with an Undiluted Phosphonium Ionic Liquid: Separations Relevant to Rare-earth Magnet Recycling. *Green Chem.* **2013**, *15*, 919-927.
79. Wellens, S.; Thijs, B.; Binnemans, K. An Environmentally Friendlier Approach to Hydrometallurgy: Highly Selective Separation of Cobalt from Nickel by Solvent Extraction with Undiluted Phosphonium Ionic Liquids. *Green Chem.* **2012**, *14*, 1657-1665.
80. Wellens, S.; Vander Hoogerstraete, T.; Möller, C.; Thijs, B.; Luyten, J.; Binnemans, K. Dissolution of Metal Oxides in an Acid-Saturated Ionic Liquid Solution and Investigation of the Back-Extraction Behaviour to the Aqueous Phase. *Hydrometallurgy* **2014**, *144-145*, 27-33.
81. Fowler, C. J.; Haverlock, T. J.; Moyer, B. A.; Shriver, J. A.; Gross, D. E.; Marquez, M.; Sessler, J. L.; Hossain, M. A.; Bowman-James, K. Enhanced Anion Exchange for Selective Sulfate Extraction: Overcoming the Hofmeister Bias. *J. Am. Chem. Soc.* **2008**, *130*, 14386-14387.

82. Patil, S. K.; Sharma, H. D. Ion Exchange and Solvent Extraction Equilibria in Mixed Electrolytes. *Can. J. Chem.* **1969**, *47*, 3851-3858.
83. Bai, L.; Wang, X.; Nie, Y.; Dong, H.; Zhang, X.; Zhang, S. Study on the Recovery of Ionic Liquids from Dilute Effluent by Electrodialysis Method and the Fouling of Cation-Exchange Membrane. *Sci. China: Chem.* **2013**, *56*, 1811-1816.
84. Abels, C.; Redepenning, C.; Moll, A.; Melin, T.; Wessling, M. Simple Purification of Ionic Liquid Solvents by Nanofiltration in Biorefining of Lignocellulosic Substrates. *J. Membr. Sci.* **2012**, *405–406*, 1-10.
85. Fernández, J. F.; Waterkamp, D.; Thöming, J. Recovery of Ionic Liquids from Wastewater: Aggregation Control for Intensified Membrane Filtration. *Desalination* **2008**, *224*, 52-56.
86. Lemus, J.; Palomar, J.; Heras, F.; Gilarranz, M. A.; Rodriguez, J. J. Developing Criteria for the Recovery of Ionic Liquids from Aqueous Phase by Adsorption with Activated Carbon. *Sep. Purif. Technol.* **2012**, *97*, 11-19.
87. Chiappe, C.; Pomelli, C. S.; Rajamani, S. Influence of Structural Variations in Cationic and Anionic Moieties on the Polarity of Ionic Liquids. *J. Phys. Chem. B* **2011**, *115*, 9653-9661.
88. Kohno, Y.; Saita, S.; Men, Y.; Yuan, J.; Ohno, H. Thermoresponsive Polyelectrolytes Derived from Ionic Liquids. *Polym. Chem.* **2015**.
89. Dupont, D.; Binnemans, K. Rare-earth Recycling Using a Functionalized Ionic Liquid for the Selective Dissolution and Revalorization of  $Y_2O_3:Eu^{3+}$  from Lamp Phosphor Waste. *Green Chem.* **2015**, *17*, 856-868.
90. Annat, G.; Forsyth, M.; MacFarlane, D. R. Ionic Liquid Mixtures—Variations in Physical Properties and Their Origins in Molecular Structure. *J. Phys. Chem. B* **2012**, *116*, 8251-8258.
91. Fukaya, Y.; Sekikawa, K.; Murata, K.; Nakamura, N.; Ohno, H. Miscibility and Phase Behavior of Water-Dicarboxylic Acid Type Ionic Liquid Mixed Systems. *Chem. Commun.* **2007**, *29*, 3089-3091.
92. Fukumoto, K.; Ohno, H. LCST-Type Phase Changes of a Mixture of Water and Ionic Liquids Derived from Amino Acids. *Angew. Chem. Int. Ed.* **2007**, *46*, 1852-1855.
93. Kohno, Y.; Arai, H.; Saita, S.; Ohno, H. Material Design of Ionic Liquids to Show Temperature-Sensitive LCST-type Phase Transition after Mixing with Water. *Aust. J. Chem.* **2011**, *64*, 1560-1567.

94. Kohno, Y.; Ohno, H. Temperature-Responsive Ionic Liquid/Water Interfaces: Relation Between Hydrophilicity of Ions and Dynamic Phase Change. *Phys. Chem. Chem. Phys.* **2012**, *14*, 5063-5070.
95. Saita, S.; Mieno, Y.; Kohno, Y.; Ohno, H. Ammonium Based Zwitterions Showing Both LCST- and UCST-type Phase Transitions After Mixing with Water in a Very Narrow Temperature Range. *Chem. Commun.* **2014**, *50*, 15450-15452.
96. Visak, Z. P.; Canongia Lopes, J. N.; Rebelo, L. P. N. Ionic Liquids in Polyethylene Glycol Aqueous Solutions: Salting-in and Salting-out Effects. *Monatsh. Chem.* **2007**, *138*, 1153-1157.
97. Il'in, K. K.; Cherkasov, D. G. Phase Equilibria and Salting-out Effects in a Cesium Nitrate-Triethylamine-Water System at 5–25 °C. *Russ. J. Phys. Chem. A* **2013**, *87*, 598-602.
98. Nockemann, P.; Thijs, B.; Parac-Vogt, T. N.; Van Hecke, K.; Van Meervelt, L.; Tinant, B.; Hartenbach, I.; Schleid, T.; Ngan, V. T.; Nguyen, M. T.; Binnemans, K. Carboxyl-Functionalized Task-Specific Ionic Liquids for Solubilizing Metal Oxides. *Inorg. Chem.* **2008**, *47*, 9987-9999.
99. Fagnant, D. P.; Goff, G. S.; Scott, B. L.; Runde, W.; Brennecke, J. F. Switchable Phase Behavior of [HBet][Tf<sub>2</sub>N]-H<sub>2</sub>O upon Neodymium Loading: Implications for Lanthanide Separations. *Inorg. Chem.* **2013**, *52*, 549-551.
100. Yang, Z. Hofmeister Effects: an Explanation for the Impact of Ionic Liquids on Biocatalysis. *J. Biotechnol.* **2009**, *144*, 12-22.

## Table of Contents Graphic

