

All-Evaporated, All-Inorganic CsPbI₃ Perovskite-based Devices for Broadband Photodetector and Solar Cell Applications

Maria Isabel Pintor Monroy^{1,2}, Iakov Goldberg^{1,2}, Karim Elkhoully^{1,2}, Epimitheas Georgitzikis¹, Lotte Clinckemalie³, Guillaume Croes^{1,2}, Nirav Annavarapu^{1,2}, Weiming Qiu^{1,3}, Elke Debroye³, Yinghuan Kuang⁴, Maarten B. J. Roeffaers⁵, Johan Hofkens^{3,6}, Robert Gehlhaar¹ and Jan Genoe^{1,2}*

¹imec, Kapeldreef 75, 3001 Leuven, Belgium

² Department of Electrical Engineering (ESAT), KU Leuven, Kasteelpark Arenberg 10, 3001 Leuven, Belgium

³ Department of Chemistry, Faculty of Sciences, KU Leuven, Celestijnenlaan 200F, 3001 Leuven, Belgium

⁴imec, partner in Solliance and Energyville, Thin Film PV, Thor Park 8320, 3600 Genk, Belgium

⁵cMACS, Department of Microbial and Molecular Systems, KU Leuven, 3001 Leuven, Belgium

⁶Max Planck Institute for Polymer Research, Ackermannweg 10, 55128 Mainz, Germany

Keywords: perovskite, inorganic, evaporated, photodetector, solar cell

Abstract: Following the rapid rise of organic metal halide perovskites towards commercial application in thin film solar cells, inorganic alternatives attracted great interest with their potential of longer device lifetime due to the stability improvement under elevated temperatures and moisture ingress. Among them, cesium lead iodide (CsPbI₃) has gained significant attention due to similar electronic and optical properties to methylammonium lead iodide (MAPbI₃), with a band gap of 1.7 eV, high absorption coefficient and large diffusion length, while also offering the advantage of being completely inorganic, providing a higher thermal stability and preventing material degradation. On a device level however, it seems also essential to replace organic

transport layers by inorganic counterparts to further prevent degradation. In addition, devices are mostly fabricated by spin coating, limiting their reproducibility and scalability; in this case, exploring all-evaporated devices allows to improve the quality of the layers and to increase their reproducibility. In this work, we focus on the deposition of CsPbI₃ by CsI and PbI₂ co-evaporation. We fabricate devices with an all-inorganic, all-evaporated structure, employing NiO and TiO₂ as transport layers, and evaluate these devices for both photodetector and solar cell applications. As a photodetector, low leakage current, high EQE and detectivity, and fast rise and decay times were obtained; while as a solar cell, acceptable efficiencies were achieved. These all-inorganic, all-evaporated devices represent one step forward towards higher stability and reproducibility, while enabling large area- compatibility and easier integration with other circuitry and, in future, the possible commercialization of perovskite-based technology.

1. Introduction

In recent years, the discovery and further emergence of methylammonium lead halide perovskites (MAPbX₃ where X = I, Br, Cl) as active layer for solar cells has pushed not only their use in the energy sector, but has also helped uncover a wide range of applications: photodetectors, light emitting diodes (LED), lasers, and radiation detectors.^{1, 2, 3, 4} Their high absorption coefficient, large diffusion length and optimal band gap make them excellent substitutes or counterparts for silicon solar cells,^{5, 6} leading to thinner active layers, and reducing the process temperature and cost.^{7, 8} The further development of MAPbI₃-based devices has made them attractive for visible-light broadband photodetectors in imagers: the reduced thickness of the active layer decreases the cross talk between adjacent pixels while high responsivities can be achieved, and the band gap larger than that of silicon reduces the unwanted response to infrared light.^{1, 9, 10, 11} However, MAPbI₃ devices can degrade over time, in presence of moisture or at higher temperatures, which represents a big challenge in the scientific community.^{5, 12}

In recent years, cesium lead iodide perovskites (CsPbI₃) have been gaining more attention, as the inorganic counterpart of MAPbI₃, for both photodetectors and solar cell applications.^{3, 13, 14} CsPbI₃ exhibits a direct band gap close to that of MAPbI₃ ($E_g = 1.7$ eV) and similar electronic and optical properties – large absorption coefficient over the

whole visible range (300-720 nm), high mobilities and long diffusion lengths – while offering the advantages of being all-inorganic: slower degradation at high temperatures or in the presence of moisture.^{15, 16, 17, 18, 19, 20} Besides the perovskite cubic α -phase, CsPbI₃ exists in other phases: an orthorhombic δ -phase (or yellow phase), an orthorhombic (or distorted cubic) γ -phase, and a tetragonal β -phase.^{14, 18, 21, 22, 23, 24} Among these, both β - and γ - phases exhibit electronic and optical properties close to those of the α -phase, and many reports refer to them in conjunction, and/or without distinction, as the “black” phase.^{24, 25, 26, 26, 27} Nevertheless, it is not the black phase but the “yellow” δ -phase the most stable at normal conditions of temperature and pressure, having a considerable larger band gap (2.8 eV), which makes it unattractive for solar cell or broadband photodetector applications.^{12, 24, 29} While the perovskite α -phase can be achieved and maintained at higher temperatures (> 300 °C), it quickly transforms to the δ -phase when exposed to moisture or when slowly cooled down, (due to the small size of the Cs cation, which cannot support the PbI₆ polyhedral frame in the cubic perovskite structure, leading to a low Goldschmidt tolerance factor)^{21, 22, 30, 31, 32} resulting in a different set of challenges, even when this transition is reversible.^{7, 29, 33} However, CsPbI₃ can remain in the black phase when stored in nitrogen, if rapidly cooled down after annealing – so-called thermal quenching – as the non-equilibrium process prevents the transition to the yellow phase by introducing stress in the lattice.^{8, 24} Several efforts have been made to “fix” the black phase and make it stable in air atmosphere, such as: introducing stabilizing agents, passivating surfaces, doping with other halides, replacing lead with indium, bismuth or tin, or reducing the grain size (i.e. nanocrystals and quantum dots);^{7, 9, 13, 16, 17, 22, 29, 31, 34} which results, in many cases, in the black phase consisting of a mix of phases or simply exhibiting the β - or γ - phases, even though is often reported as α -phase.^{27, 35, 36} Nevertheless, more work must be done to position CsPbI₃- based devices at the level of the MAPbI₃- based ones. So far, most of the deposition methods involve spin coating of the perovskite, which limits the reproducibility of the devices and their scalability over large areas. The use of organic or polymer stabilizing agents brings back the disadvantages inherent to organic materials, reducing the devices stability and limiting their operation in harsh environments.³⁴ Furthermore, recent device work focuses mainly on the modification of the perovskite layer, while using the same organic layers that are used in MAPbI₃-based solar cell structures: poly (3,4-ethylenedioxythiophene) polystyrene sulfonate

(PEDOT:PSS), 2,2',7,7'-tetrakis [N,N-di(4-methoxyphenyl)amino]-9,9'-spirobifluorene (spiro-OMeTAD), poly[bis(4-phenyl) (2,4,6-trimethylphenyl)amine] (PTAA), poly(3-hexylthiophene) (P3HT) as hole transport layers (HTL) and [6,6]-phenyl-C₆₁-butyric acid methyl ester (PCBM) or 2,9-dimethyl-4,7-diphenyl-1,10-phenanthroline (BCP) as electron transport layers (ETL).^{3, 5, 7, 37} The application of organic transport layers is limiting the advantages of using an inorganic perovskite. In the case of inorganic transport layers, two main materials have been explored for both MAPbX₃ and CsPbX₃ devices: mesoporous or compact TiO₂ as ETL, commonly deposited by spin coating,^{3, 17, 22, 30} and NiO as HTL, mainly deposited by magnetron sputtering or pulsed laser deposition and utilized in inverted devices;^{38, 39, 40} regardless, the implementation of both TiO₂ and NiO in the same structure is not common. In this paper, we evaluate the deposition of CsPbI₃ by thermal evaporation in a co-evaporation approach, offering good thickness control and reproducibility. Post-deposition annealing and fast cool down are subsequently combined to “fix” the black phase in a moisture-free atmosphere.³⁷ Additionally, we investigate the use of evaporated inorganic transport layers to obtain all-inorganic, all-evaporated devices with solar cell and broadband – in the whole visible range – photodetector applications. The introduction of all-evaporated layers in a simple structure allows for a better control of the layers thickness, decreasing the number of defects and improving the quality of the interfaces between layers, while increasing the reproducibility of the devices and enabling their large area scalability.^{37, 39} On the other side, while being all-inorganic, the devices could be operated in harsh environments and at higher temperature ranges with limited degradation, while uniform inorganic contact layers can also act as effective barrier layers to protect the active layer against moisture and oxygen.

2. Results and Discussion

For the fabrication of the perovskite films, we apply a co-evaporation approach of CsI and PbI₂ as described in the experimental section. As-deposited samples exhibit a dark brown color, which has previously been attributed to the γ -phase; this phase is obtained at low substrate temperatures and is a feature unique to the evaporation technique, for stoichiometric or CsI-rich samples.^{8, 18, 37} Even when the γ -phase (which has also been referred as α' -phase) is present at room temperature under nitrogen atmosphere, it exhibits a slightly larger band gap than the α -phase,^{8, 12} and it irreversibly transforms to

the δ phase at temperatures higher than 150 °C or when exposed to air and humidity. To obtain the reversible black phase, samples were annealed inside a glove box in two steps: first, at 150 °C until they transition to the δ phase, and second, at 335 °C to obtain the desired black phase. Afterwards, samples were rapidly cooled down by placing them on a metallic surface, to fix the black phase at room temperature. This annealing in a temperature range between 310 – 330 °C, followed by a rapid cool down, has been carried out for previously reported evaporated films, either by co-evaporation,^{8, 41} or by a layer-by-layer approach.^{5, 37, 42} **Figure 1a** shows the photographs of a film as it goes through the different phases: the as-deposited films (bottom) are brown, transitioning to yellow when they are annealed at 150 °C (middle) and then to a darker, almost black, color (top) when annealed at 335 °C. The absorbance and photoluminescence (PL) spectra for the different phases can be observed in Figure 1b. The as-deposited film and the film annealed at 335 °C exhibit very similar spectra for both absorbance and PL, with the latter having a slightly narrower band gap (1.7 eV, as calculated from the Tauc plot) and a PL emission peak at 706 nm. These values are in agreement with values previously reported in literature for spin coated and evaporated black CsPbI₃ films.^{21, 34, 37} The difference between the PL emission peak and the band gap value is due to a Stokes shift of ~47 meV, related to the vibrational relaxation of the lattice and is in agreement with values reported for MAPbBr₃ and CsPbBr₃.⁴³ Films in the yellow phase (annealed at 150 °C) have a considerably larger band gap (2.8 eV) and exhibit a broadband (400-800 nm) emission spectrum. Absorbance spectrum agrees with values previously reported.¹⁶ There is almost no information about the PL spectrum of the yellow phase, as is not as interesting for the scientific community as the black phases are; however, a broadband emission has also been reported.^{16, 44}

X-ray diffraction (XRD) patterns corresponding to the three different phases observed in the films were also obtained and shown in Figure 1c. For this, it was important to understand how the films grow on the substrates used for the device fabrication, as results can considerably differ from the growth of films on glass.^{45, 46, 47} Films were deposited on glass/ITO/NiO substrates and subjected to the post-annealing as described above. The XRD spectra are compared with references from literature; references for α - and β - phases correspond to previous reports that discuss the synthesis and differentiation of β - phase CsPbI₃,^{14, 26, 48} while patterns for both δ - and γ - phases have been obtained from Straus et al. work.⁴⁹ As it can be seen, the as-deposited films

(bottom) exhibit two very broad peaks, related to their nanostructured nature and can be mostly assigned to the CsPbI₃ γ -phase, as previously reported for as-deposited evaporated films, with the main peak located at $\sim 28^\circ$.^{12, 18} As the films are annealed at 150 °C, a shift in the main peak towards lower angles can be observed, corresponding to the transition to δ -phase. The peak is still broad, indicating there is no considerable change in the crystallite size of the films. This transition also agrees with previous evaporation reports.^{12, 18} Finally, when the films are annealed at 335 °C, a new transition occurs. In this case, not only the peaks become sharper and narrower, a change in preferential orientation is also present, when compared with as-deposited films. Two double peaks can be observed, at around 14.5-15° and then again at 28-30°. These features of double peaks - and a shift of peaks to larger angles due to stress generated by the fast cool down that the films are subjected to or due to the substrates - complicate the determination of the α -, β - or γ -phases in annealed films, as all phases share main peaks at similar angles. It can be argued that, by rapidly cooling down the films after annealing, a partial transition from the perovskite phase to quasi-perovskite β - or γ -phases occur and the films are a mix of all the black phases; something that has been discussed before.^{24,37,49} The origin of this mix is due to the transition of the α -phase to the other black phases (β - or γ -phases) as it cools down, before converting back to yellow.¹⁴ The crystalline structure of the “fix” black phase then depends on the cooling method (in this case, a fast cooling using a metal surface) and the layers below the perovskite. More importantly, no typical peaks corresponding to the yellow phase were observed. When compared with other black CsPbI₃ deposited by co-evaporation, Burwig et al. observed the black phase and determined it to be α -phase in films deposited on glass and annealed, however, their films also exhibit some peaks which they could not identify as belonging to the α -phase, and which angles seem to be corresponding to the γ -phase. They also observed a shifting in the main peak towards lower angles. This evidence agrees with our findings and is pointing to a mix of phases instead of the α -phase as they have claimed.¹² Hutter et al. deposited CsPbI₃ films on quartz and, after annealing, besides a shifting of the peaks due to the stress while cooling down, peaks corresponding to PbI₂ could also be identified, indicating that they had excess of PbI₂ in their films.³⁷ It is worth noting that the XRD of the films reported here is for films grown on top of glass/ITO/NiO, to represent the films that are used for

the devices and, as mentioned before, we do not observe any peak corresponding to the yellow CsPbI₃ phase nor to PbI₂ or CsI precursors.

To determine the thickness of the black CsPbI₃ films, variable angle spectroscopic ellipsometry (VASE) measurements were performed, and the values of the refractive index (n) and extinction coefficient (k) were obtained by fitting Ψ and Δ values to the adequate model constructed using the commercially available software CompleteEASE (J.A. Woollam). The resulting values of n and k are shown in **Figure 2a**. Although there are not many reports in literature, these values agree with values recently reported by Yan et al.²¹ With the determined optical constants and the application of transfer matrix simulations, we optimized the device architecture by targeting maximum light absorption with a low active layer thickness. The optimum perovskite film thickness was determined to 260 nm. Atomic force microscopy (AFM) was used to measure the roughness of the films, deposited on glass/ITO/NiO and with a TiO₂ layer on top of the perovskite, to prevent its conversion to the δ -phase during measurements in air. According to the AFM images (Figure 2b), the grains are large in size with an average diameter of 1 μ m, which helps decreasing the amount of defects and traps accumulated in the grain boundaries.³⁹ The average roughness was calculated as \sim 20 nm, which is a considerable improvement from previously reported evaporated films, and closer to the roughness reported for spin coated films.^{8, 21, 37}

Devices were fabricated using the CsPbI₃ layer as the active layer. For this, ITO was used as the bottom electrode, NiO was selected as HTL, TiO₂ as ETL and aluminum as top contact, as described in the experimental section. Both TiO₂ and NiO have been explored for several MAPbX₃- and CsPbX₃- based devices, although independently and usually not evaporated.³⁸ In this case, NiO was deposited by reactive magnetron sputtering on top of ITO, controlling the resistivity of the films by controlling the amount of oxygen during deposition. This approach to obtain NiO films has been reported before.^{50, 51} TiO₂ was deposited by reactive e-beam evaporation with an oxygen partial pressure of 1×10^{-4} mbar, to compensate vacancies created during deposition as previously used for MAPbI_{3-x}Cl_x-based solar cells.⁵² Figure 2c shows the band diagram for the device. As it can be seen, NiO besides working as HTL, offers a high electron affinity, working as electron blocking layer (EBL);^{50, 53} at the same time, TiO₂ is acting as hole blocking layer (HBL).^{54, 55} Using both, NiO and TiO₂, allows to achieve low leakage current while keeping a simple structure. Figure 2d shows the full device cross

section obtained by scanning electron microscopy (SEM). From the image, it is observed that all layers are compact and continuous; with the perovskite having the aimed thickness and being dense and without cracks. This is an improvement when compared with spin coated devices without additives or ligands, where pin holes, defects or low densities can be found.³³ The image also shows that the deposition of TiO₂ by e-beam does not damage the perovskite below, with a clean interface between layers.

Figure 3a shows the diode J - V curves in dark, for both forward and reverse sweep. Low leakage current ($\sim 10^{-7}$ A/cm²) at low negative voltage (- 0.5 V) has been achieved, which is necessary for the photodetector lower detection limit. However, devices exhibit hysteresis, as is common with perovskite-based devices.⁵⁶ In addition to low leakage current, high EQE is also needed for high photodetector and solar cell performances. EQE indicates the probability of generating a charge carrier in the photodetector upon incident light.³⁴ The EQE spectra (Figure 3b) show high EQE for all visible wavelengths below the perovskite band gap, even at 0 V, and reaching saturation at a negative bias of - 0.5 V. This means that no larger negative voltages are needed to obtain a high EQE and, therefore, the device can perform in photodetector mode at a low negative bias, where the leakage current is low, and low light intensities can be detected. The obtained values of EQE are in agreement with values reported in literature for both spin coated and evaporated devices.^{8, 9, 17, 30}

Besides EQE, for the application of the devices as photodetectors, responsivity R and specific detectivity D^* are important figures of merit. Responsivity tells how efficient an optical signal is transformed into an electrical signal by the photodetector and is defined as the amount of current that can be produced per Watt of incident illumination at a given wavelength (A/W), which is given by:^{9, 19, 57}

$$R = \frac{I_{ph}}{P_{opt}} \text{ (A/W)} \quad (1)$$

Where I_{ph} is the produced photocurrent and P_{opt} is the optical power. Responsivity is linked to EQE through the equation:^{32, 57}

$$R = \frac{e}{hc/\lambda} * EQE \quad (2)$$

Where e is the electron charge, h is Planck's constant, c is the speed of light and λ is the incoming wavelength.

Specific detectivity describes the ability of a device to detect weak signals in presence of noise and is determined by both, the device responsivity and the noise current, or noise equivalent power (NEP), as $D^* = \sqrt{(A \Delta f)/NEP}$. Considering that shot noise is the main contributor to the NEP in dark, and that the contributions of Johnson and flick noise are insignificant, then D^* can be defined as:^{32, 57, 58}

$$D^* = R/(2eJ_{dark})^{1/2} \quad (\text{cmHz}^{1/2}\text{W}^{-1}), \quad (3)$$

where J_{dark} is the dark current density of the device. EQE, R and D^* are plotted for the device when biased at -0.5 V (Figure 3c). Both R and D^* values are considerably higher than other CsPbI₃-based photodetectors, calculated as 0.4 A/W and 2.4×10^{12} cmHz^{1/2}W⁻¹ (or Jones), respectively, for wavelengths in the 650-680 nm range. These values correspond to the obtained high EQE and imply a good conversion of photons to charge carriers and their collection at the contacts. EQE higher than 100% (gain) is impossible to achieve without the presence of traps that generate a multiplying effect and is less common for a photodiode structure when compared with phototransistors or photoconductors.^{57, 58}

The device performance as solar cell is shown in Figure 3d. In similarity to the J - V in dark, the J - V curves in light also present normal hysteresis – when FF and/or V_{oc} values are higher for reverse sweep – with devices exhibiting an efficiency of 8.84% for reverse sweep and 7.90% for forward sweep.⁵⁶ This difference in the efficiency is due to the difference in the open circuit voltage (V_{oc}) values, measured as 0.93 V and 0.86 V, respectively. CsPbI₃-based devices fabricated by spin coating or co-evaporation exhibit the same hysteresis, with higher V_{oc} values for the reverse sweep curves.^{8, 17} Besides V_{oc} , short-circuit current (J_{sc}) and fill factor (FF) values were obtained as 14.3 mA/cm² and 59% for forward sweep and 14.3 mA/cm² and 68% for reverse sweep. Even when J_{sc} values are in agreement with values reported for CsPbI₃, they are lower than values obtained for MAPbI₃, which is mostly related to the difference in the band gap of the materials.^{8, 17, 37} Statistics for different devices are shown in **Figure 4**, for both forward and reverse sweep. The average efficiency was calculated as 7.3% for forward sweep and as 7.9% for reverse sweep, with a standard deviation of 0.3% and 0.4%, respectively. Despite the fact that these efficiencies are lower than efficiencies reported for spin coated devices using organic transport layers and organic surface passivating agents or by partially replacing Pb with other elements such as In (10-17%),^{17, 22, 30, 31} results agree with spin coated devices without further treatment ($\eta = 8\%$, $J_{sc} = 16$

mA/cm², $V_{oc} = 0.89$ V, FF = 57%),³⁰ and with devices using an evaporated CsPbI₃ but with organic layers (7-9%).^{5, 8, 37, 41} Talking about the exhibited hysteresis, this phenomenon has been attributed to the device architecture, the materials used and even to the test conditions. For example, the use of planar TiO₂ when compared with mesoporous TiO₂ has been discussed as source of hysteresis, as mesoporous TiO₂ offers a larger contact area with the perovskite, which leads to more efficient electron transfer and separation.⁵⁶ Similar hysteresis has been observed when using e-beam evaporated TiO₂ for MAPbI_{3-x}Cl₃ solar cells.⁵² However, the use of mesoporous TiO₂ also leads to higher leakage current, which is unwanted for photodetector applications.³ Another reason for hysteresis might be related to the presence of traps, leading to non-radiative recombination. In this case, non-radiative recombination losses should be further minimized, by both improving the quality of the perovskite and by passivating the interface between layers.⁵⁶ This will also lead to a larger V_{oc} , and to achieve higher efficiencies.^{29, 59} However, the devices reported here show promising results for being all-inorganic, all-evaporated devices based on CsPbI₃. More importantly, these devices can be operated as solar cell or photodetector without any change in the device structure or fabrication.

The application of the devices as photodetectors was further evaluated by obtaining their response to a 530 nm wavelength LED while varying the light intensity (**Figure 5a**). As expected, the photocurrent of the devices increases as the light intensity increases, with a linear response, indicating a stable responsivity (inset). From these curves, the responsivity of the device to different light intensities and at different voltages was obtained (Figure 5b). Responsivity values are in agreement with the obtained EQE for the 530 nm wavelength. The responsivity of the devices remains fairly constant regardless of the light intensity and the applied negative voltage, which is a good indicator of the quality of the devices. However, responsivity slightly decreases towards low light intensities, explained by traps being filled, although this effect is rather small. The larger decrease of R towards larger negative voltages for low light intensities is linked to the larger leakage current at said values. However, for $V \geq -1.5$ V, the devices are well-behaved. Moreover, as the devices exhibit a saturated EQE at -0.5 V, there is no need to bias them at even lower voltages. Figure 5c shows the values of R, EQE and D^* for the device biased at -0.5 V and under different light intensities. As it can be seen, the device is well-behaved throughout the whole range of

light intensities, with high values of EQE and R for the 530 nm wavelength. The values of D^* are also high, showing the ability of the device to respond to low light intensities.

Finally, it is important to also determine the speed of the devices. Besides exhibiting high responsivity and detectivity, fast response times broaden the application range. The speed of the devices is determined by their rise (τ_r , 10 - 90%) and decay time (τ_d , 90 - 10%).² Figure 5d shows the multi-cycle transient photoresponse of the devices while being illuminated with a 530 nm wavelength LED at low light intensities. For a device with an active area of 0.025 cm², τ_r and τ_d were calculated as 7 and 8 μ s, respectively. From τ_r values, the 3 dB cut-off frequency (f_{3dB}) can be calculated. This f_{3dB} corresponds to the input light frequency at which the output signal is 3 dB lower than the signal of the continuous wave modulation,⁹ and is given by:^{60, 61}

$$f_{3dB} \approx 0.35/\tau_r \text{ (Hz)} \quad (4)$$

From this, f_{3dB} was calculated as 50 kHz, which is fast enough for imagers applications.¹¹ However, to obtain faster response and, therefore, larger f_{3dB} , the dimensions of the photodetectors can be further decreased from these large area devices, by reducing the capacitance values of the photodiode and, in result, reducing the RC time constant of the detector.^{60, 62}

The performance of the photodetectors reported here is comparable with spin coated MAPbI₃-based devices, exhibiting similar leakage current, detectivity, EQE and responsivity values.^{2, 39, 60} Moreover, the promising performance is also demonstrated when comparing with other CsPbI₃-based detectors. Devices based on polymer-wrapped CsPbI₃ exhibit a breakdown voltage of – 0.4 V, considerably lower responsivity and EQE, with values of 0.1 W/A and 25%, respectively, and similar rise and decay times.³⁴ CsPbI₃ photodetectors based on metal-semiconductor-metal (MSM) interdigitated structures exhibit considerably higher rise and decay time, measured as 24 and 29 ms, respectively.¹³ For phototransistors, even when the obtained responsivity is orders of magnitude higher, the required voltage applied at the gate (V_G) goes up to – 60 V, and the response time can be in the range of seconds. Furthermore, the devices exhibit gain at low light intensities, which results in a non-constant responsivity.¹⁵ Comparing with CsPbI₃ photodiodes reported by Sim et al., both devices exhibit similar leakage current; however, their devices are 2x thicker than the devices reported here, while their responsivity is 10x smaller and their f_{3dB} about 7x smaller.⁹ **Table 1** shows a

comparison between the devices reported here and other CsPbI₃-based photodetectors previously reported. A comparison of different device structures based on the device rise time vs responsivity is also displayed in **Figure 6**, demonstrating that devices with higher responsivity are also considerably slower while devices that exhibit a faster response have lower responsivity. As it can be seen, the devices reported in this work show promising results as photodetectors, with high responsivity, specific detectivity and fast response.

3. Conclusions

Summarized, we have demonstrated all-inorganic all-vacuum-evaporated CsPbI₃ perovskite-based devices and their application as broadband photodetectors and solar cells. The different layers were deposited either by sputtering, thermal, or e-beam evaporation, enabling integration in large area electronics by precise process parameter control and high through-put. Films are dense with a low roughness of ~20 nm, according to AFM images. Devices show low leakage current, $\sim 10^{-7}$ A/cm² at -0.5 V, with EQE higher than 70% over the entire visible range. Additionally, devices show high responsivity, 0.2 - 0.4 A/W, and high specific detectivity, 1 - 2 cmHz^{1/2}W⁻¹, in the visible light range. Of special interest for imagers are the high detectivity for low light intensity detection and a constant responsivity over a broad range of light intensities. The speed of these devices was also measured, with a rise and decay time of 7 and 8 μ s, respectively, which can be further improved by decreasing the detector area. Benchmarking with already existing CsPbI₃ photodetectors exhibits the potential of this fabrication and architecture concept. Finally, the versatility of the exact same devices has been demonstrated by evaluating their performance as solar cells, with efficiencies in the range of 7 - 8%. Even though, this efficiency is lower than CsPbI₃-based solar cells that are deposited by spin coating and passivated using organic ligands, it can be further improved by tuning the interfaces between layers. We believe that these full-evaporated CsPbI₃-based devices can in the future combine high performance with long term stability due to their fully inorganic nature.

4. Experimental section

Perovskite deposition: CsPbI₃ thin films were deposited by thermal evaporation from the co-evaporation of CsI (abcr, ultra-dry) and PbI₂ (TCI Chemicals) precursors, calibrating the deposition rate of each precursor based on a 1:1 CsI to PbI₂ molar ratio for stoichiometric films. The precursor deposition rates were calibrated by ellipsometry

(RC2, J.A.Woollam). The evaporation system was fabricated in-house, with a source to substrate distance of ~ 30 cm and shutters for both sources and substrate. During deposition, the substrate was fixed in one position and heated up to 60 °C. After deposition, brown as-deposited samples were obtained, linked to the γ -phase. To obtain and fix the cubic α -phase, samples were annealed inside a glovebox first at 150 °C and then at 335 °C until they transition to yellow and then to black, respectively. After that, samples were cooled down rapidly by placing them on a metallic surface in order to fix the black phase.

Device fabrication: For the devices, 3×3 cm² glass substrates with pre-patterned ITO strips (15Ω , Colorado Concept Coatings) were cleaned in an ultrasonic bath using Extran, water, acetone, and isopropanol, in that order, and dried out using a nitrogen gun. As HTL, 15 nm thick NiO films were deposited on top of the substrates by reactive sputtering in a Nebula system from Angstrom Engineering Inc., with a metallic nickel target and introducing oxygen during deposition. Samples were then annealed at 300 °C in air for 30 min and annealed again for 30 min at 150 °C inside a glovebox, to remove any adsorbed humidity before the perovskite deposition. Afterwards, 260 nm thick CsPbI₃ films were deposited and annealed as described above. As ETL, 85 nm thick TiO₂ films were deposited by e-beam evaporation in a high vacuum system (Angstrom Engineering Inc.), introducing oxygen during deposition to compensate oxygen vacancies, and keeping the deposition rate at 0.3 Å/s to prevent damage to the perovskite film. Finally, 80 nm thick Al contacts were deposited by thermal evaporation and using a shadow mask, keeping a low deposition rate of 0.3 Å/s. After the perovskite deposition, devices were always kept under nitrogen atmosphere to prevent the perovskite conversion to the yellow phase when exposed to air and humidity.

Device characterization: To characterize the perovskite films, absorbance, ellipsometer, and PL measurements were performed in air to obtain band gap, absorption spectra, refractive index and extinction coefficient, thickness, and PL spectra. Absorbance spectra were obtained using a Shimadzu UV1601 spectrophotometer. Ellipsometry measurements were performed in a Woollam RC2 ellipsometer and PL spectra for both films exhibiting black phases were performed using a Hamamatsu Quantaurs-Tau Fluorescence lifetime spectrometer and using a green (530 nm) excitation laser. Because the Hamamatsu system was not equipped with a laser with shorter wavelength, to obtain the PL spectrum for the yellow CsPbI₃ phase (with a band

gap of 2.8 eV) a different set-up was used. In this case, the PL spectrum was captured by applying 355 nm pump light from a CryLaS FTSS 355-300 laser onto a spot of 600 μm diameter. The laser was pulsed at the rate of 20Hz and was attenuated to an energy of 62 μJ per pulse. The resultant PL spectrum was captured by sending this light into the Princeton Instruments SpectraPro HRS-500 Spectrograph. To obtain the XRD patterns, measurements of the as-deposited films, films annealed at 150 $^{\circ}\text{C}$ and films annealed at 335 $^{\circ}\text{C}$ were recorded with a Malvern PANalytical Empyrean diffractometer in reflection mode, using a PIXcel3D solid-state detector and a Cu anode (Cu $K_{\alpha 1}$: 1.5406 \AA ; Cu $K_{\alpha 2}$: 1.5444 \AA). The measurements were performed in a 2θ range between 10 $^{\circ}$ and 40 $^{\circ}$, with a step size of 0.026 $^{\circ}$ at 200 s/step, in nitrogen atmosphere and at room temperature. AFM images were obtained using a Bruker Dimension Edge system to evaluate the films roughness; the measurements were carried out in air, using TiO_2 as capping layer, to prevent the perovskite transition during the measurement. SEM images were obtained using an FEI Nova 200 system to evaluate the cross section of the full devices, and images were artificially colored for easier identification of the layers.

For the electrical and optical characterization of the devices, all measurements were carried out in a nitrogen atmosphere. J - V curves in dark and under illumination were obtained by measuring the devices using a probe station in a glove box, connected to an Agilent 4156C Semiconductor Parameter Analyzer. To obtain the response of the devices under different light intensities, a M530L2 green (530 nm) LED from Thorlabs was used, at ~ 20 cm from the device and varying the light intensity with a Thorlabs DC2200 LED driver. The light intensity was calibrated using a Si photodiode. The performance of the device as solar cell was evaluated by using an Abet solar simulator under 100 mW/cm^2 (1 sun) simulated AM 1.5G illumination. For the rise and decay time, devices were encapsulated to be measured in air. The devices were biased at -0.5 V and illuminated with a M530L2 green (530 nm) LED from Thorlabs, 5 cm from the device, and controlled by the Thorlabs DC2200 LED driver. In this case, a light intensity of 30%, a frequency of 10 kHz and a 50:50 duty cycle were used. The output signal was converted to voltage and amplified using a Femto DHPA-100 variable gain high speed current amplifier and collected using a Keysight DSO6102A oscilloscope. EQE measurements were performed using a Bentham PV300 spectral response system,

with a Xenon/Quartz halogen lamp and a Bentham TMc300 single monochromator. Measurements were calibrated using a Si photodiode.

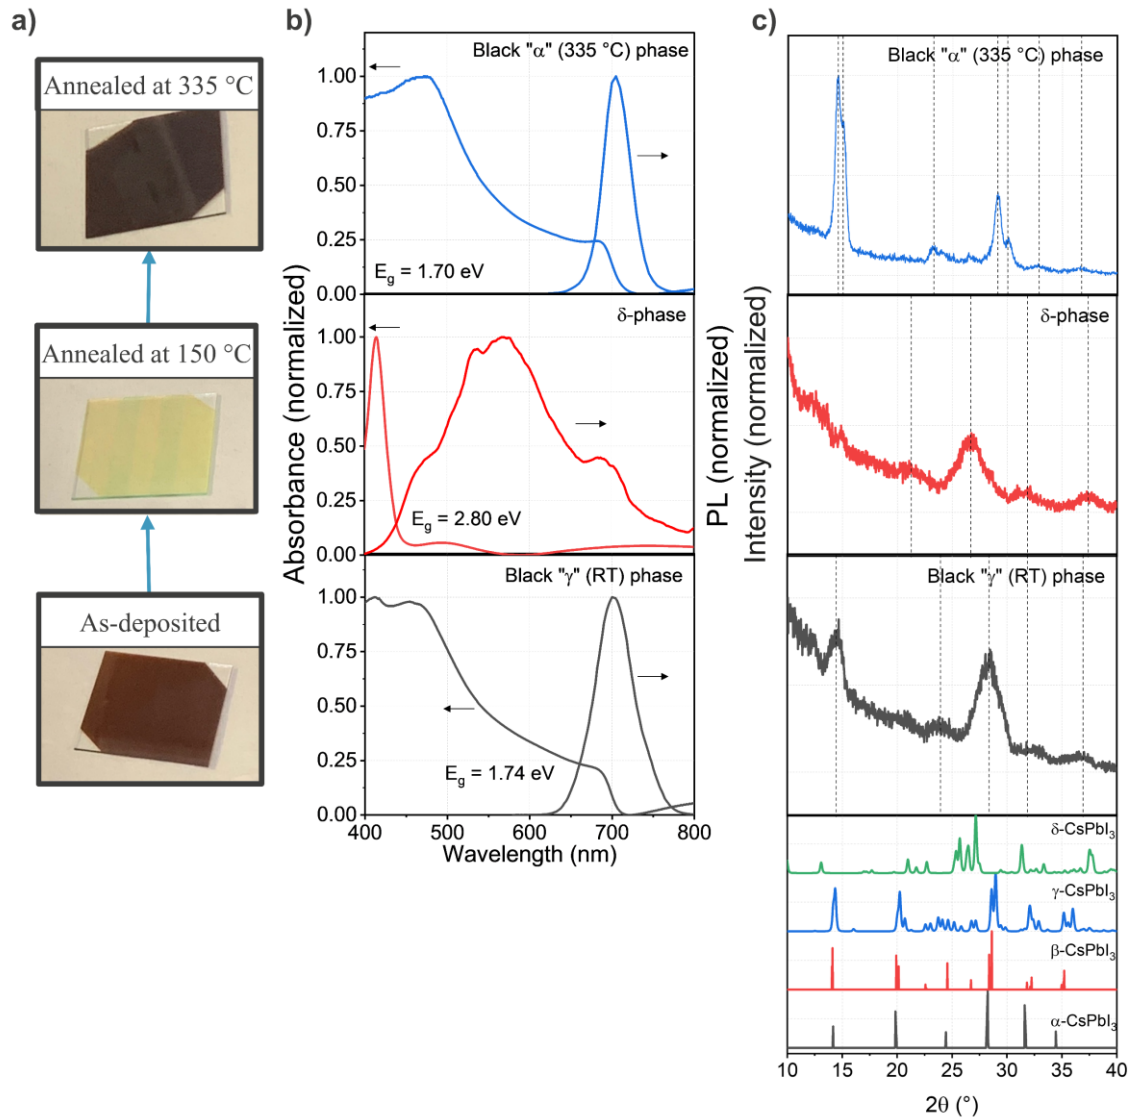


Figure 1. a) Photographs of 3x3 cm² substrates of the transitions CsPbI₃ films: the as-deposited film (bottom) exhibits a dark brown color, which transitions to yellow as the film is annealed at 150 °C (middle); finally, when the film is annealed at 335 °C (top) it exhibits a darker, almost black, color. b) Corresponding absorbance and photoluminescence spectra for each of the phases: the as-deposited film and film annealed at 335 °C show very similar absorbance and PL spectrum, while the annealed film has a slightly narrower band gap. The films annealed at 150 °C have a notably larger band gap and a broadband emission spectrum. c) Comparison of the XRD spectra for the three CsPbI₃ phases. The as-deposited film has very broad peaks that indicate a nanocrystalline structure, and that corresponds to the γ -phase. The film annealed at 150 °C also exhibits broad peaks but corresponding to the δ -phase. Finally, the spectrum for the films annealed at 335 °C show sharper, narrower peaks, indicating larger crystallite

size. The presence of a double peak at $\sim 15^\circ$ and again at $\sim 28^\circ$, indicates that this film does not belong completely to the α - phase but to a mix of phases.

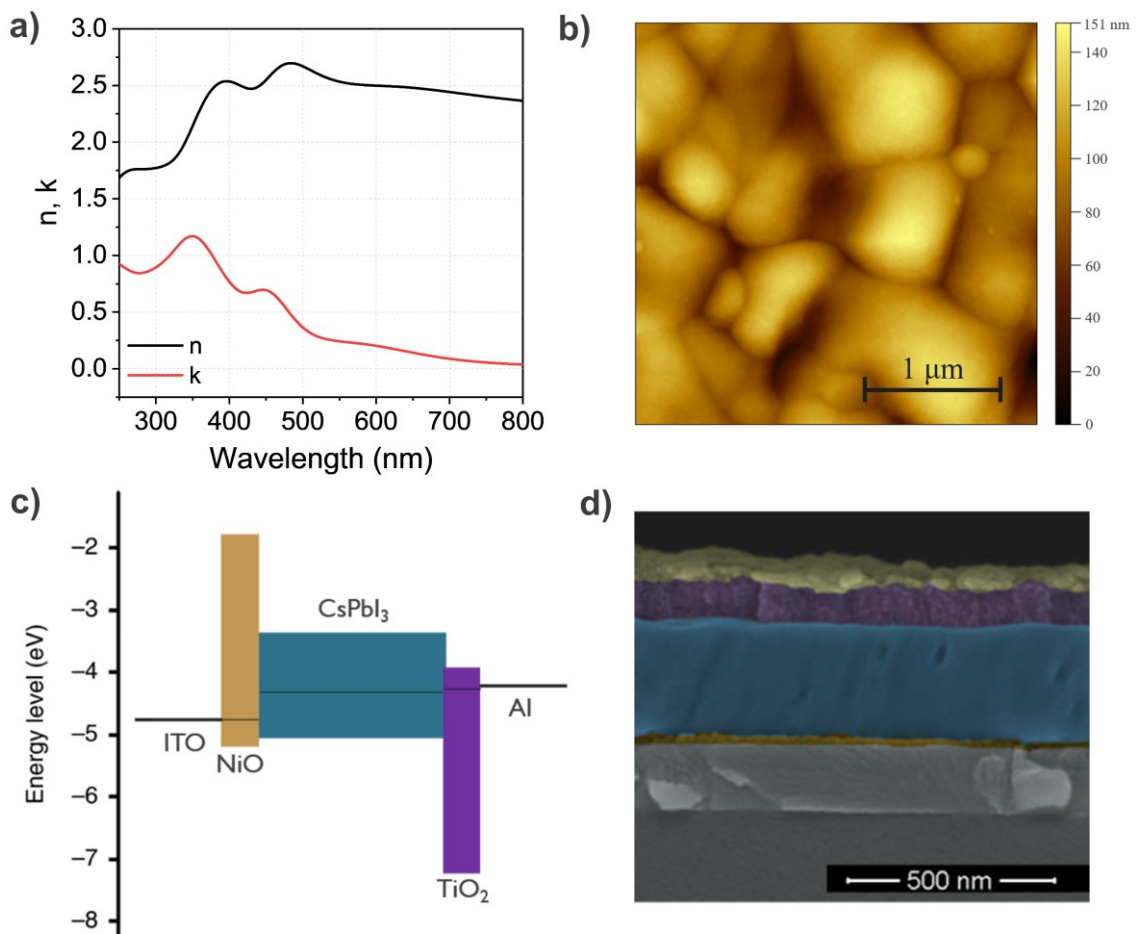


Figure 2. a) Values of n and k for the black phase of CsPbI₃. b) AFM images showing the roughness of the perovskite films, with an average root mean square roughness of 22 nm. c) CsPbI₃-based device band diagram, using NiO and TiO₂ as transport layers. d) Device SEM cross section, the interface between layers is clean and the perovskite is dense and without short circuits.

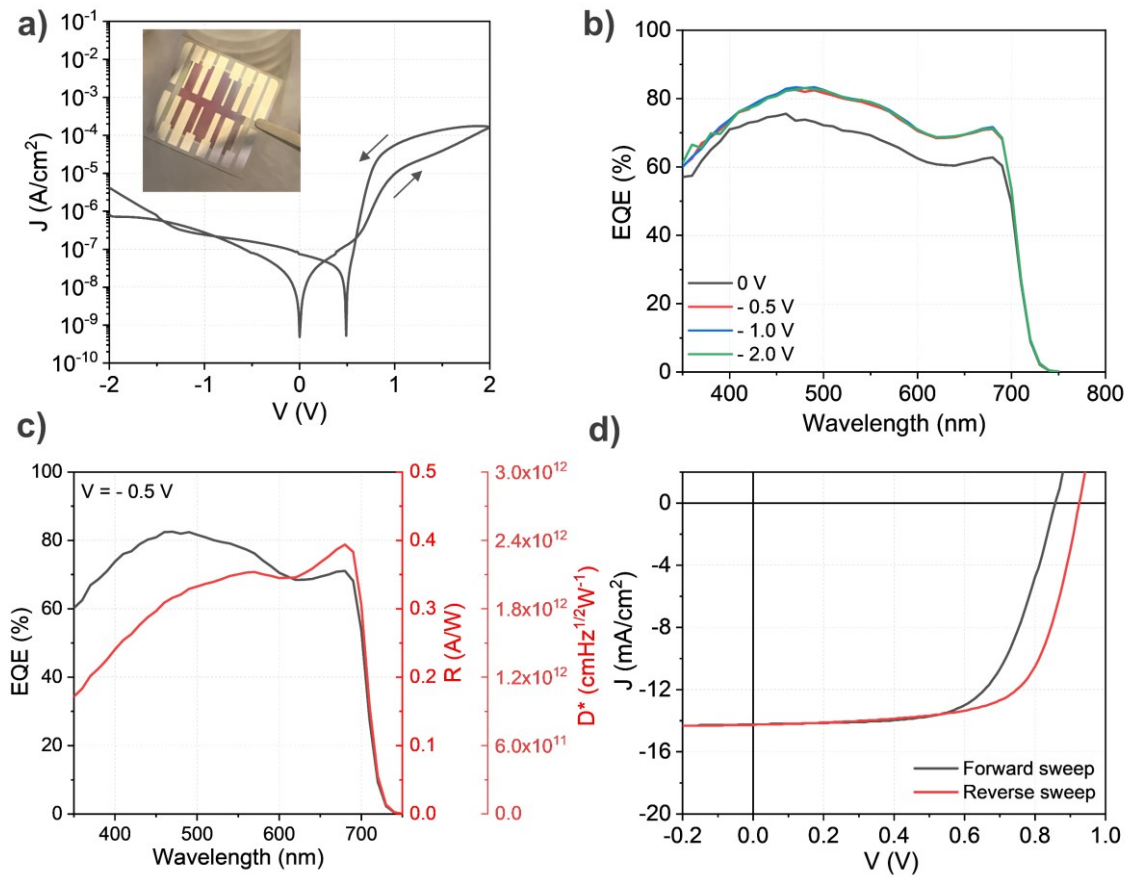


Figure 3. a) Device JV curves in dark, for both forward and reverse sweep. The device exhibits hysteresis, as commonly happens with perovskite-based devices. Inset shows a photograph of a finished sample. b) EQE vs wavelength for the device when biased at different voltages. Saturation is reached at a negative bias of -0.5 V. c) EQE, R and D^* for the device when biased at -0.5 V. d) Solar cell performance for both forward and reverse sweep. Efficiency of 7-8% was achieved.

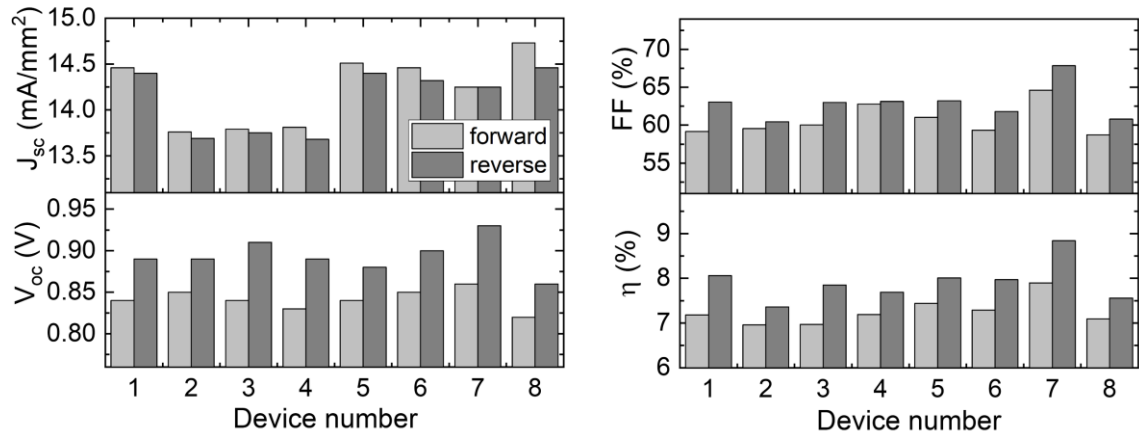


Figure 4. Statistics for several CsPbI₃-based solar cells, for both forward and reverse sweep.

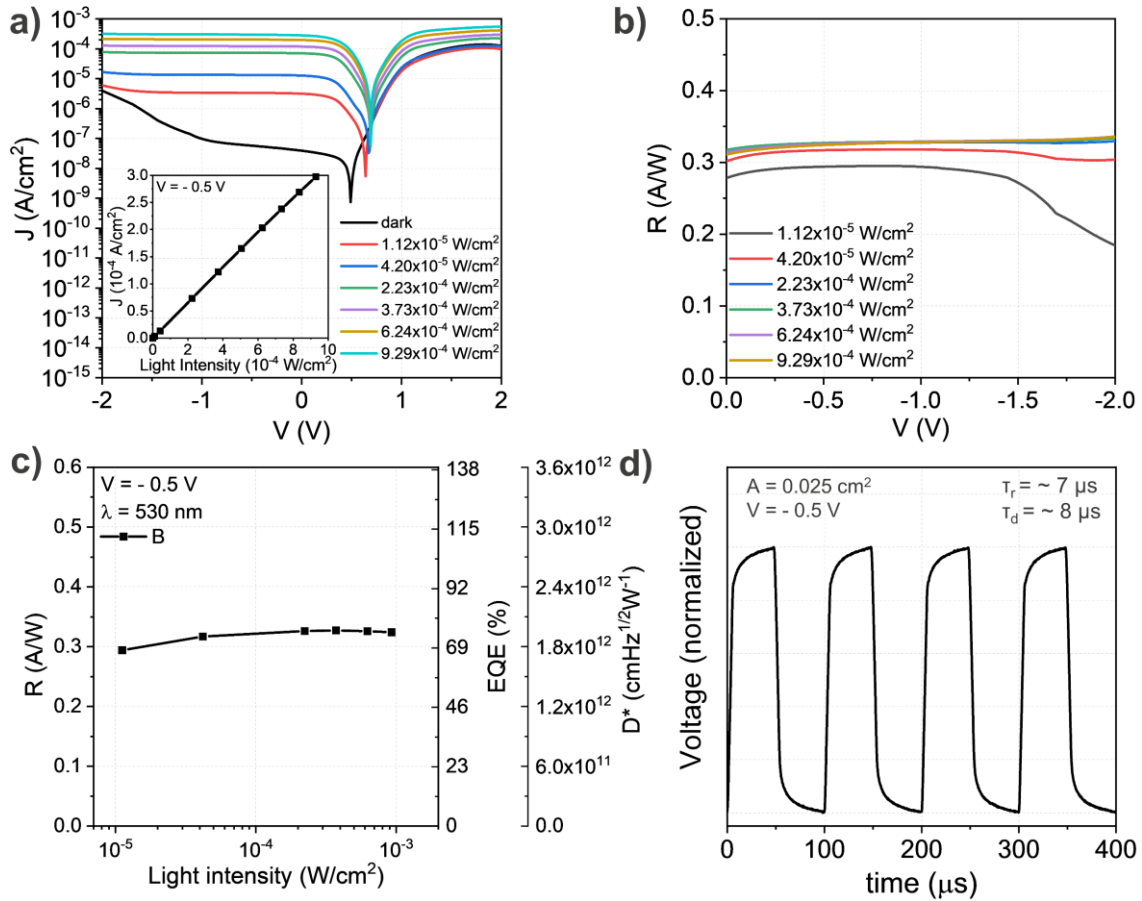


Figure 5. a) CsPbI₃ photodetector performance when illuminated with a 530 nm LED at different light intensities. Inset shows the linear behavior of the current density with the light intensity, exhibiting a constant responsivity at -0.5 V. b) Responsivity vs voltage curve for different light intensities. Responsivity values are constant in the range of 0 to -1.5 V. c) Photodetector R , EQE and D^* values for different light intensities when illuminated with a 530 nm LED and biased at -0.5 V. Devices are well-behaved throughout the whole range of light intensities. d) Time-dependent photoresponse when the device is biased at -0.5 V. Rise and decay time are in the range of 7-8 μ s for a size of 0.025 cm².

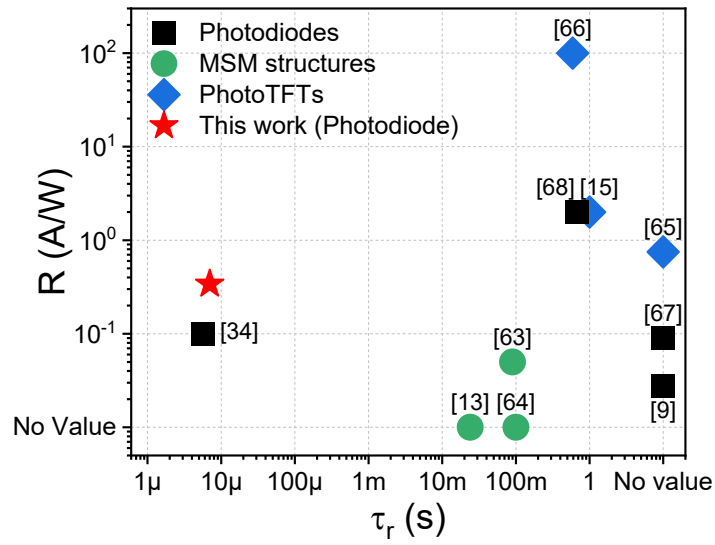


Figure 6. Comparison of the performance, in terms of rise time and responsivity, of the CsPbI₃-based photodetector reported here with other CsPbI₃-based photodetectors reported in literature (references are added to each graph point). As it can be seen, the responsivity is higher than most MSM and photodiodes while the rise time is faster than most of the devices previously reported.

Table 1. Comparison of the performance of the CsPbI₃-based devices reported here with other CsPbI₃-based photodetectors previously reported in literature. (PV = CsPbI₃)

Device	Method	Structure	J_d (A/cm ²)	R (A/W)	EQE (%)	D^* (cmHz ^{1/2} W ⁻¹)	τ_r/τ_d	Ref.
Au/PV/Au	SC	MSM	--	--	--	6.29×10^{11}	24/29 ms	13
Au/CsPbI ₂ Br/Au	SC	MSM	--	~ 0.05 @ 520 nm	--	$\sim 5.5 \times 10^{11}$	90/110 ms	63
FTO/PV/FTO	SC	MSM	--	--	--	--	100/100 ms	64
Si/SiO ₂ /PV/C8BTBT/ Au	DC	photoTFT	$\sim 10^{-11}$ A	~ 2 @ -30 V (white light)	--	--	seconds	15
Si/SiO ₂ /PV/Au	drop casting	photoTFT	$\sim 10^{-9}$ A @ -0.2V	~ 0.75 @ 530 nm	--	$\sim 3.5 \times 10^{10}$	--	65
Si/SiO ₂ /MoS ₂ /CsPbI _{1-x} Br _x /Au	SC	photoTFT	$\sim 10^{-11}$ A	~ 100 @ -60 V (532 nm)	10^4	$\sim 10^9$	0.59/0.32 s	66
ITO/SnO ₂ /PV/Au	SC	photodiode	--	0.1 @ 550 nm	25 @ 550 nm	1.0×10^{12}	5.7/6.2 μ s	34
ITO/ZnO/PV/P3HT/ MoO ₃ /Ag	SC	photodiode	10^{-7} @ -0.5V	0.028 @ 550 nm	--	1.6×10^{12}	--	9
FTO/TiO ₂ /PV/Spiro- OMeTAD/Ag	SC	photodiode	10^{-7} @ -0.8V	0.09 @ 550 nm	--	1×10^{13} @ 0V	--	67
ITO/ZnO/PbS/TBAI/ PV/Au	SC	photodiode	10^{-7} @ -1V	~ 2 @ -1 V (white light)	--	$\sim 4 \times 10^{12}$	0.68/0.45 s	68
ITO/NiO/PV/TiO ₂ /Al	evapora tion	photodiode	10^{-7} @ -0.5V	0.34 @ 530 nm	80 @ 530 nm	2×10^{12}	7/8 μ s	this work

* SC = Spin Coating, DC = Dip-coating

AUTHOR INFORMATION

Corresponding Author

Maria Isabel Pintor-Monroy^{1,2*}

¹imec, Kapeldreef 75, 3001 Leuven, Belgium

² Department of Electrical Engineering (ESAT), KU Leuven, Kasteelpark Arenberg 10, 3001 Leuven, Belgium

E-mail: isabel.pintormonroy@imec.be

Author Contributions

The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript.

Funding Sources

The authors acknowledge funding from the European Research Council (ERC) under the European Union's Horizon 2020 research and innovation programme (grant agreement No 835133 "ULTRA-LUX"). W.Q. and E.D. would like to thank the Research Foundation Flanders (FWO) for financial support through postdoctoral fellowship grants (grant number for W.Q. 12Z4618N and for E.D. 12O3719N). G.C. and L.C. are supported via a PhD fellowship of the FWO (grant numbers for L.C. 1SA0821N and for G.C. 1S91520N).

J.H acknowledges financial support from the Research Foundation Flanders (FWO Grant Numbers G.0B39.15, G.0B49.15, G098319N, S002019N and ZW15_09-GOH6316), the KU Leuven Research Fund through iBOF funding (PERsist: iBOF-21-085), the Flemish government through long-term structural funding Methusalem (CASAS2, Meth/15/04) and the MPI as MPI fellow.

REFERENCES

- (1) Mei, F.; Sun, D.; Mei, S.; Feng, J.; Zhou, Y.; Xu, J.; Xiao, X. Recent Progress in Perovskite-Based Photodetectors: The Design of Materials and Structures. *Advances in Physics: X* **2019**, *4* (1), 1592709.
- (2) Zhao, Y.; Li, C.; Shen, L. Recent Research Process on Perovskite Photodetectors: A Review for Photodetector—Materials, Physics, and Applications. *Chinese Phys. B* **2018**, *27* (12), 127806.
- (3) Zhang, C.; Kuang, D.; Wu, W. A Review of Diverse Halide Perovskite Morphologies for Efficient Optoelectronic Applications. *Small Methods* **2020**, *4* (2), 1900662.
- (4) Stylianakis, M.; Maksudov, T.; Panagiotopoulos, A.; Kakavelakis, G.; Petridis, K. Inorganic and Hybrid Perovskite Based Laser Devices: A Review. *Materials* **2019**, *12* (6), 859.
- (5) Kottokkaran, R.; Gaonkar, H. A.; Bagheri, B.; Dalal, V. L. Efficient P-i-n Inorganic CsPbI₃ Perovskite Solar Cell Deposited Using Layer-by-Layer Vacuum Deposition. *Journal of Vacuum Science & Technology A* **2018**, *36* (4), 041201.
- (6) Hamada, K.; Yonezawa, K.; Yamamoto, K.; Taima, T.; Hayase, S.; Ooyagi, N.; Yamamoto, Y.; Ohdaira, K. Vacuum Deposition of CsPbI₃ Layers on Textured Si for Perovskite/Si Tandem Solar Cells. *Jpn. J. Appl. Phys.* **2019**, *58* (SB), SBBF06.
- (7) Ahmad, W.; Khan, J.; Niu, G.; Tang, J. Inorganic CsPbI₃ Perovskite-Based Solar Cells: A Choice for a Tandem Device. *Sol. RRL* **2017**, *1* (7), 1700048.
- (8) Frolova, L. A.; Anokhin, D. V.; Piryazev, A. A.; Luchkin, S. Yu.; Dremova, N. N.; Stevenson, K. J.; Troshin, P. A. Highly Efficient All-Inorganic Planar Heterojunction Perovskite Solar Cells Produced by Thermal Coevaporation of CsI and PbI₂. *J. Phys. Chem. Lett.* **2017**, *8* (1), 67–72.
- (9) Sim, K. M.; Swarnkar, A.; Nag, A.; Chung, D. S. Phase Stabilized α -CsPbI₃ Perovskite Nanocrystals for Photodiode Applications. *Laser & Photonics Reviews* **2018**, *12* (1), 1700209.
- (10) Johnston, M. B. Colour-Selective Photodiodes. *Nature Photon* **2015**, *9* (10), 634–636.
- (11) Lin, Q.; Armin, A.; Lyons, D. M.; Burn, P. L.; Meredith, P. Low Noise, IR-Blind Organohalide Perovskite Photodiodes for Visible Light Detection and Imaging. *Adv. Mater.* **2015**, *27* (12), 2060–2064.
- (12) Burwig, T.; Fränzel, W.; Pistor, P. Crystal Phases and Thermal Stability of Co-Evaporated CsPbX₃ (X = I, Br) Thin Films. *J. Phys. Chem. Lett.* **2018**, *9* (16), 4808–4813.
- (13) Ramasamy, P.; Lim, D.-H.; Kim, B.; Lee, S.-H.; Lee, M.-S.; Lee, J.-S. All-Inorganic Cesium Lead Halide Perovskite Nanocrystals for Photodetector Applications. *Chem. Commun.* **2016**, *52* (10), 2067–2070.
- (14) Marronnier, A.; Roma, G.; Boyer-Richard, S.; Pedesseau, L.; Jancu, J.-M.; Bonnassieux, Y.; Katan, C.; Stoumpos, C. C.; Kanatzidis, M. G.; Even, J. Anharmonicity and Disorder in the Black Phases of Cesium Lead Iodide Used for Stable Inorganic Perovskite Solar Cells. *ACS Nano* **2018**, *12* (4), 3477–3486.
- (15) Chen, Y.; Wu, X.; Chu, Y.; Zhou, J.; Zhou, B.; Huang, J. Hybrid Field-Effect Transistors and Photodetectors Based on Organic Semiconductor and CsPbI₃ Perovskite Nanorods Bilayer Structure. *Nano-Micro Lett.* **2018**, *10* (4), 57.
- (16) Waleed, A.; Tavakoli, M. M.; Gu, L.; Hussain, S.; Zhang, D.; Poddar, S.; Wang, Z.; Zhang, R.; Fan, Z. All Inorganic Cesium Lead Iodide Perovskite Nanowires with Stabilized Cubic Phase at Room Temperature and Nanowire Array-Based Photodetectors. *Nano Lett.* **2017**, *17* (8), 4951–4957.

- (17) Li, B.; Zhang, Y.; Fu, L.; Yu, T.; Zhou, S.; Zhang, L.; Yin, L. Surface Passivation Engineering Strategy to Fully-Inorganic Cubic CsPbI₃ Perovskites for High-Performance Solar Cells. *Nat Commun* **2018**, *9* (1), 1076.
- (18) Becker, P.; Márquez, J. A.; Just, J.; Al-Ashouri, A.; Hages, C.; Hempel, H.; Jošt, M.; Albrecht, S.; Frahm, R.; Unold, T. Low Temperature Synthesis of Stable Γ -CsPbI₃ Perovskite Layers for Solar Cells Obtained by High Throughput Experimentation. *Adv. Energy Mater.* **2019**, *9* (22), 1900555.
- (19) Yang, T.; Li, F.; Zheng, R. Recent Progress on Cesium Lead Halide Perovskites for Photodetection Applications. *ACS Appl. Electron. Mater.* **2019**, *1* (8), 1348–1366.
- (20) Zhang, H.; Debroye, E.; Steele, J. A.; Roeffaers, M. B. J.; Hofkens, J.; Wang, H. I.; Bonn, M. Highly Mobile Large Polarons in Black Phase CsPbI₃. *ACS Energy Lett.* **2021**, *6* (2), 568–573.
- (21) Yan, W.; Guo, Y.; Beri, D.; Dottermusch, S.; Chen, H.; Richards, B. S. Experimental Determination of Complex Optical Constants of Air-Stable Inorganic CsPbI₃ Perovskite Thin Films. *Phys. Status Solidi RRL* **2020**, *14* (6), 2000070.
- (22) Li, Z.; Zhou, F.; Wang, Q.; Ding, L.; Jin, Z. Approaches for Thermodynamically Stabilized CsPbI₃ Solar Cells. *Nano Energy* **2020**, *71*, 104634.
- (23) Sutton, R. J.; Filip, M. R.; Haghighirad, A. A.; Sakai, N.; Wenger, B.; Giustino, F.; Snaith, H. J. Cubic or Orthorhombic? Revealing the Crystal Structure of Metastable Black-Phase CsPbI₃ by Theory and Experiment. *ACS Energy Lett.* **2018**, *3* (8), 1787–1794.
- (24) Steele, J. A.; Jin, H.; Dovgaliuk, I.; Berger, R. F.; Braeckvelt, T.; Yuan, H.; Martin, C.; Solano, E.; Lejaeghere, K.; Rogge, S. M. J.; Notebaert, C.; Vandezande, W.; Janssen, K. P. F.; Goderis, B.; Debroye, E.; Wang, Y.-K.; Dong, Y.; Ma, D.; Saidaminov, M.; Tan, H.; Lu, Z.; Dyadkin, V.; Chernyshov, D.; Van Speybroeck, V.; Sargent, E. H.; Hofkens, J.; Roeffaers, M. B. J. Thermal Unequilibrium of Strained Black CsPbI₃ Thin Films. *Science* **2019**, *365* (6454), 679–684.
- (25) Zhao, H.; Xu, J.; Zhou, S.; Li, Z.; Zhang, B.; Xia, X.; Liu, X.; Dai, S.; Yao, J. Preparation of Tortuous 3D Γ -CsPbI₃ Films at Low Temperature by CaI₂ as Dopant for Highly Efficient Perovskite Solar Cells. *Adv. Funct. Mater.* **2019**, 1808986.
- (26) Wang, K.; Tian, Q.; Zhao, G.; Wen, J.; Huang, J.; Gao, C.; Xu, Z.; Liu, Y.; Liang, L.; Meng, L.; Zhang, L.; Liu, Z.; Jin, Z.; Olthof, S.; Liu, S. (Frank). Beach-Chair-Shaped Energy Band Alignment for High-Performance β -CsPbI₃ Solar Cells. *Cell Reports Physical Science* **2020**, *1* (9), 100180.
- (27) Shen, Q.; Ripolles, T. S.; Even, J.; Ogomi, Y.; Nishinaka, K.; Izuishi, T.; Nakazawa, N.; Zhang, Y.; Ding, C.; Liu, F.; Toyoda, T.; Yoshino, K.; Minemoto, T.; Katayama, K.; Hayase, S. Slow Hot Carrier Cooling in Cesium Lead Iodide Perovskites. *Appl. Phys. Lett.* **2017**, *111* (15), 153903.
- (28) Chang, X.; Fang, J.; Fan, Y.; Luo, T.; Su, H.; Zhang, Y.; Lu, J.; Tsetseris, L.; Anthopoulos, T. D.; Liu, S. (Frank); Zhao, K. Printable CsPbI₃ Perovskite Solar Cells with PCE of 19% via an Additive Strategy. *Adv. Mater.* **2020**, *32* (40), 2001243.
- (29) Ho-Baillie, A.; Zhang, M.; Lau, C. F. J.; Ma, F.-J.; Huang, S. Untapped Potentials of Inorganic Metal Halide Perovskite Solar Cells. *Joule* **2019**, *3* (4), 938–955.

- (30) Hu, Y.; Bai, F.; Liu, X.; Ji, Q.; Miao, X.; Qiu, T.; Zhang, S. Bismuth Incorporation Stabilized α -CsPbI₃ for Fully Inorganic Perovskite Solar Cells. *ACS Energy Lett.* **2017**, *2* (10), 2219–2227.
- (31) Li, X.; Wang, K.; Lgbari, F.; Dong, C.; Yang, W.; Ma, C.; Ma, H.; Wang, Z.-K.; Liao, L.-S. Indium Doped CsPbI₃ Films for Inorganic Perovskite Solar Cells with Efficiency Exceeding 17%. *Nano Res.* **2020**, *13* (8), 2203–2208.
- (32) Wang, H.; Kim, D. H. Perovskite-Based Photodetectors: Materials and Devices. *Chem. Soc. Rev.* **2017**, *46* (17), 5204–5236.
- (33) Liu, C.; Yang, Y.; Xia, X.; Ding, Y.; Arain, Z.; An, S.; Liu, X.; Cristina, R. C.; Dai, S.; Nazeeruddin, M. K. Soft Template-Controlled Growth of High-Quality CsPbI₃ Films for Efficient and Stable Solar Cells. *Adv. Energy Mater.* **2020**, *10* (9), 1903751.
- (34) Bansode, U.; Rahman, A.; Ogale, S. Low-Temperature Processing of Optimally Polymer-Wrapped α -CsPbI₃ for Self-Powered Flexible Photo-Detector Application. *J. Mater. Chem. C* **2019**, *7* (23), 6986–6996.
- (35) Eperon, G. E.; Paternò, G. M.; Sutton, R. J.; Zampetti, A.; Haghighirad, A. A.; Cacialli, F.; Snaith, H. J. Inorganic Caesium Lead Iodide Perovskite Solar Cells. *J. Mater. Chem. A* **2015**, *3* (39), 19688–19695.
- (36) Haque, F.; Wright, M.; Mahmud, M. A.; Yi, H.; Wang, D.; Duan, L.; Xu, C.; Upama, M. B.; Uddin, A. Effects of Hydroiodic Acid Concentration on the Properties of CsPbI₃ Perovskite Solar Cells. *ACS Omega* **2018**, *3* (9), 11937–11944.
- (37) Hutter, E. M.; Sutton, R. J.; Chandrashekar, S.; Abdi-Jalebi, M.; Stranks, S. D.; Snaith, H. J.; Savenije, T. J. Vapour-Deposited Cesium Lead Iodide Perovskites: Microsecond Charge Carrier Lifetimes and Enhanced Photovoltaic Performance. *ACS Energy Lett.* **2017**, *2* (8), 1901–1908.
- (38) Higgins, M.; Reyes-Banda, M. G.; Martínez-Falomir, G. G.; Bouanani, L. E.; Murillo, B.; Chavez-Urbiola, I. R.; Pintor-Monroy, M. I.; Ely, F.; Mathew, X.; Quevedo-Lopez, M. A. Solvent-Free and Large Area Compatible Deposition of Methylammonium Lead Bromide Perovskite by Close Space Sublimation and Its Application in PIN Diodes. *Thin Solid Films* **2019**, *692*, 137585.
- (39) Dong, Y.; Zou, Y.; Song, J.; Song, X.; Zeng, H. Recent Progress of Metal Halide Perovskite Photodetectors. *J. Mater. Chem. C* **2017**, *5* (44), 11369–11394.
- (40) Shan, Q.; Li, J.; Song, J.; Zou, Y.; Xu, L.; Xue, J.; Dong, Y.; Huo, C.; Chen, J.; Han, B.; Zeng, H. All-Inorganic Quantum-Dot Light-Emitting Diodes Based on Perovskite Emitters with Low Turn-on Voltage and High Humidity Stability. *J. Mater. Chem. C* **2017**, *5* (18), 4565–4570.
- (41) Chen, C.-Y.; Lin, H.-Y.; Chiang, K.-M.; Tsai, W.-L.; Huang, Y.-C.; Tsao, C.-S.; Lin, H.-W. All-Vacuum-Deposited Stoichiometrically Balanced Inorganic Cesium Lead Halide Perovskite Solar Cells with Stabilized Efficiency Exceeding 11%. *Adv. Mater.* **2017**, *29* (12), 1605290.
- (42) Yonezawa, K.; Yamamoto, K.; Shahiduzzaman, Md.; Furumoto, Y.; Hamada, K.; Ripolles, T. S.; Karakawa, M.; Kuwabara, T.; Takahashi, K.; Hayase, S.; Taima, T. Annealing Effects on CsPbI₃-Based Planar Heterojunction Perovskite Solar Cells Formed by Vacuum Deposition Method. *Jpn. J. Appl. Phys.* **2017**, *56* (4S), 04CS11.
- (43) Guo, Y.; Yaffe, O.; Hull, T. D.; Owen, J. S.; Reichman, D. R.; Brus, L. E. Dynamic Emission Stokes Shift and Liquid-like Dielectric Solvation of Band Edge Carriers in Lead-Halide Perovskites. *Nat Commun* **2019**, *10* (1), 1175.

- (44) Chen, Z.; Dong, L.; Tang, H.; Yu, Y.; Ye, L.; Zang, J. Direct Synthesis of Cubic Phase CsPbI₃ Nanowires. *CrystEngComm* **2019**, *21* (9), 1389–1396.
- (45) Lu, Y.; Han, Q.; Zhao, Y.; Yang, C.; Li, Y.; Liu, X. Substrate-Dependent Growth of CH₃NH₃PbI₃ Films Deposited by Vacuum Evaporation. *J. Phys.: Conf. Ser.* **2020**, *1637*, 012080.
- (46) Deng, Y.-H. Substrate Engineering in the Growth of Perovskite Crystals. *arXiv:2010.04422 [cond-mat]* **2020**.
- (47) Olthof, S.; Meerholz, K. Substrate-Dependent Electronic Structure and Film Formation of MAPbI₃ Perovskites. *Sci Rep* **2017**, *7* (1), 40267.
- (48) Wang, Y.; Dar, M. I.; Ono, L. K.; Zhang, T.; Kan, M.; Li, Y.; Zhang, L.; Wang, X.; Yang, Y.; Gao, X.; Qi, Y.; Grätzel, M.; Zhao, Y. Thermodynamically Stabilized β -CsPbI₃-Based Perovskite Solar Cells with Efficiencies >18%. *Science* **2019**, *365* (6453), 591–595.
- (49) Straus, D. B.; Guo, S.; Cava, R. J. Kinetically Stable Single Crystals of Perovskite-Phase CsPbI₃. *J. Am. Chem. Soc.* **2019**, *141* (29), 11435–11439.
- (50) Pintor-Monroy, M. I.; Murillo-Borjas, B. L.; Catalano, M.; Quevedo-Lopez, M. A. Controlling Carrier Type and Concentration in NiO Films To Enable *in Situ* PN Homojunctions. *ACS Appl. Mater. Interfaces* **2019**, *11* (30), 27048–27056.
- (51) Park, J.-W.; Park, J.-W.; Jung, K.; Yang, M. K.; Lee, J.-K. Influence of Oxygen Content on Electrical Properties of NiO Films Grown by Rf Reactive Sputtering for Resistive Random-Access Memory Applications. *J. Vac. Sci. Technol. B* **2006**, *24* (5), 2205.
- (52) Qiu, W.; Paetzold, U. W.; Gehlhaar, R.; Smirnov, V.; Boyen, H.-G.; Tait, J. G.; Conings, B.; Zhang, W.; Nielsen, C. B.; McCulloch, I.; Froyen, L.; Heremans, P.; Cheyns, D. An Electron Beam Evaporated TiO₂ Layer for High Efficiency Planar Perovskite Solar Cells on Flexible Polyethylene Terephthalate Substrates. *J. Mater. Chem. A* **2015**, *3* (45), 22824–22829.
- (53) Pintor-Monroy, M. I.; Barrera, D.; Murillo-Borjas, B. L.; Ochoa-Estrella, F. J.; Hsu, J. W. P.; Quevedo-Lopez, M. A. Tunable Electrical and Optical Properties of Nickel Oxide (NiO_x) Thin Films for Fully Transparent NiO_x-Ga₂O₃ p-n Junction Diodes. *ACS Appl. Mater. Interfaces* **2018**, *10* (44), 38159–38165.
- (54) Yu, I.-S.; Wang, Y.-W.; Cheng, H.-E.; Yang, Z.-P.; Lin, C.-T. Surface Passivation and Antireflection Behavior of ALD on N-Type Silicon for Solar Cells. *International Journal of Photoenergy* **2013**, *2013*, 1–7.
- (55) Marques, F. C.; Jasieniak, J. J. Ionization Potential and Electron Attenuation Length of Titanium Dioxide Deposited by Atomic Layer Deposition Determined by Photoelectron Spectroscopy in Air. *Applied Surface Science* **2017**, *422*, 504–508.
- (56) Liu, P.; Wang, W.; Liu, S.; Yang, H.; Shao, Z. Fundamental Understanding of Photocurrent Hysteresis in Perovskite Solar Cells. *Adv. Energy Mater.* **2019**, *9* (13), 1803017.
- (57) Baeg, K.-J.; Binda, M.; Natali, D.; Caironi, M.; Noh, Y.-Y. Organic Light Detectors: Photodiodes and Phototransistors. *Adv. Mater.* **2013**, *25* (31), 4267–4295.
- (58) Pintor-Monroy, M. I.; Murillo-Borjas, B. L.; Quevedo-Lopez, M. A. Nanocrystalline and Polycrystalline β -Ga₂O₃ Thin Films for Deep Ultraviolet Detectors. *ACS Appl. Electron. Mater.* **2020**, *2*(10), 3358–3365.
- (59) Luo, D.; Su, R.; Zhang, W.; Gong, Q.; Zhu, R. Minimizing Non-Radiative Recombination Losses in Perovskite Solar Cells. *Nat Rev Mater* **2020**, *5* (1), 44–60.

- (60) Fang, Y.; Huang, J. Resolving Weak Light of Sub-Picowatt per Square Centimeter by Hybrid Perovskite Photodetectors Enabled by Noise Reduction. *Adv. Mater.* **2015**, *27* (17), 2804–2810.
- (61) Tong, G.; Li, H.; Li, D.; Zhu, Z.; Xu, E.; Li, G.; Yu, L.; Xu, J.; Jiang, Y. Dual-Phase CsPbBr₃-CsPb₂Br₅ Perovskite Thin Films via Vapor Deposition for High-Performance Rigid and Flexible Photodetectors. *Small* **2018**, *14* (7), 1702523.
- (62) Goushcha, A. O.; Tabbert, B. On Response Time of Semiconductor Photodiodes. *Opt. Eng* **2017**, *56* (09), 1.
- (63) Liu, Z.; Li, H.; Qin, C.; Zhang, T.; Gu, Y.; Chen, H.; Zheng, H.; Li, S. Solution-Processed Inorganic Perovskite Flexible Photodetectors with High Performance. *Nanoscale Res Lett* **2019**, *14* (1), 284.
- (64) Liang, J.; Wang, C.; Zhao, P.; Lu, Z.; Ma, Y.; Xu, Z.; Wang, Y.; Zhu, H.; Hu, Y.; Zhu, G.; Ma, L.; Chen, T.; Tie, Z.; Liu, J.; Jin, Z. Solution Synthesis and Phase Control of Inorganic Perovskites for High-Performance Optoelectronic Devices. *Nanoscale* **2017**, *9* (33), 11841–11845.
- (65) Zhou, Y.; Luo, J.; Zhao, Y.; Ge, C.; Wang, C.; Gao, L.; Zhang, C.; Hu, M.; Niu, G.; Tang, J. Flexible Linearly Polarized Photodetectors Based on All-Inorganic Perovskite CsPbI₃ Nanowires. *Advanced Optical Materials* **2018**, *6* (22), 1800679.
- (66) Wu, H.; Si, H.; Zhang, Z.; Kang, Z.; Wu, P.; Zhou, L.; Zhang, S.; Zhang, Z.; Liao, Q.; Zhang, Y. All-Inorganic Perovskite Quantum Dot-Monolayer MoS₂ Mixed-Dimensional van Der Waals Heterostructure for Ultrasensitive Photodetector. *Adv. Sci.* **2018**, *5* (12), 1801219.
- (67) Bi, C.; Kershaw, S. V.; Rogach, A. L.; Tian, J. Improved Stability and Photodetector Performance of CsPbI₃ Perovskite Quantum Dots by Ligand Exchange with Aminoethanethiol. *Adv. Funct. Mater.* **2019**, *29* (29), 1902446.
- (68) Saleem, M. I.; Yang, S.; Batool, A.; Sulaman, M.; Veeramalai, C. P.; Jiang, Y.; Tang, Y.; Cui, Y.; Tang, L.; Zou, B. CsPbI₃ Nanorods as the Interfacial Layer for High-Performance, All-Solution-Processed Self-Powered Photodetectors. *Journal of Materials Science & Technology* **2020**, S1005030220308835.

For Table of Contents only

